

Titre: Microstructural origins of crushing strength for inherently anisotropic brittle materials

Auteurs: David Cantor, Carlos Ovalle, & Émilien Azéma

Date: 2022

Type: Article de revue / Article

Référence: Cantor, D., Ovalle, C., & Azéma, É. (2022). Microstructural origins of crushing strength for inherently anisotropic brittle materials. International Journal of Solids and Structures, 238, 111399 (12 pages).
Citation: <https://doi.org/10.1016/j.ijsolstr.2021.111399>

Document en libre accès dans PolyPublie

Open Access document in PolyPublie

URL de PolyPublie: <https://publications.polymtl.ca/10818/>

Version: Version finale avant publication / Accepted version
Révisé par les pairs / Refereed

Conditions d'utilisation: Creative Commons Attribution-Utilisation non commerciale-Pas d'oeuvre dérivée 4.0 International / Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International (CC BY-NC-ND)

Document publié chez l'éditeur officiel

Document issued by the official publisher

Titre de la revue: International Journal of Solids and Structures (vol. 238)

Maison d'édition: Elsevier

URL officiel: <https://doi.org/10.1016/j.ijsolstr.2021.111399>

Mention légale: © 2022. This is the author's version of an article that appeared in International Journal of Solids and Structures (vol. 238) . The final published version is available at <https://doi.org/10.1016/j.ijsolstr.2021.111399>. This manuscript version is made available under the CC-BY-NC-ND 4.0 license <https://creativecommons.org/licenses/by-nc-nd/4.0/>

Microstructural origins of crushing strength for inherently anisotropic brittle materials

David Cantor^{a,b,*}, Carlos Ovalle^{a,b}, Emilien Azéma^{c,d}

^a*Department of Civil, Geological and Mining Engineering, Polytechnique Montreal, Montreal, QC, Canada*

^b*Research Institute of Mining and Environment, RIME UQAT-Polytechnique, Montreal, QC, Canada*

^c*LMGC, Université de Montpellier, CNRS, Montpellier, France*

^d*Institut Universitaire de France (IUF), Paris, France*

Abstract

We study the crushing strength of brittle materials whose internal structure (e.g., mineral particles or grains) presents a layered arrangement reminiscent of sedimentary and metamorphic rocks. Taking a discrete-element approach, we probe the failure strength of circular-shaped samples intended to reproduce specific mineral configurations. To do so, assemblies of cells, products of a modified Voronoi tessellation, are joined in mechanically-stable layerings using a bonding law. The cells' shape distribution allows us to set a level of inherent anisotropy to the material. Using a diametral point loading, and systematically changing the loading orientation with respect to the cells' configuration, we characterize the failure strength of increasingly anisotropic structures. This approach lets us reproduce experimental observations regarding the shape of the failure strength curve, the Weibull modulus, failure patterns of rocks, and quantify the consumption of the fragmentation energy, and the induced anisotropies linked to the cell's geometry and force transmission in the samples. Based on a fine description of geometrical and mechanical properties at the onset of failure, we develop a micromechanical breakdown of the crushing strength variability using an analytical decomposition of the stress tensor and the geometrical and force anisotropies. We

*Corresponding author

Email addresses: david.cantor@tpolymtl.ca (David Cantor), carlos.ovalle@polymtl.ca (Carlos Ovalle), emilien.azema@umontpellier.fr (Emilien Azéma)

can conclude that the origins of failure strength in anisotropic layered media rely on compensations of geometrical and mechanical anisotropies, as well as an increasing average radial force between minerals indistinctive of tensile or compressive components.

Keywords: fabric, anisotropy, failure strength, Weibull statistics, fragmentation energy, discrete element method

1. Introduction

The mechanical behavior of many solids can be tracked down to the level of molecules, defects, and dislocations that may cause stress concentrations and yielding of the material. However, the microstructural level can be equally or more important for characterizing their failure strength. Imagine, for instance, arrangements produced by the genesis, layering, and stratification of a solid such as sedimentation, rock metamorphism, or even crystal growth. In these cases, the mechanical properties are not determined at the molecular level but instead at the microstructural level [1].

We focus on the failure strength of brittle materials, which may include rocks, soil grains, ceramics, and even ice. In the case of rock masses and rock aggregates, for example, it is well known that the mechanical behavior depends on mineralogy and grain characteristics (e.g., size and shape distribution of minerals), matrix level of cementation, joint characteristics, and fissuring [2]. Many of these geometrical attributes are also called *fabric* or *microstructure* for geological materials. If any of those fabric properties present a preferred orientation or organization in space, then the material can be considered inherently anisotropic. Many studies have focused on the quantification of the level of inherent fabric anisotropy in rocks or on the impact of the loading orientation on the ultimate strength of such layered materials [3, 4, 5, 6, 7, 8, 9, 10, 11].

In experiments, cylindrical cores are often used to characterize the failure strength of inherently anisotropic rocks under diametrical point loading (commonly called *Brazilian test*). In those tests, the orientation θ of the applied force is gradually varied with respect to the orientation of the internal layering (see Fig. 1). For such a circular geometry, axial symmetry is found along the layering orientation; then, the failure strength can be fully characterized by varying θ in the range $[0^\circ, 90^\circ]$. Note as well that the rock cores and test configurations are chosen, so the inherently anisotropic con-

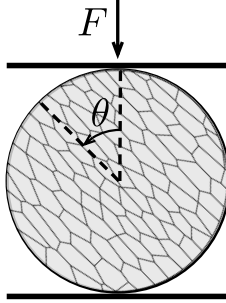


Figure 1: Scheme of a diametrical loading in which the loading orientation varies relative to the orientation of the internal structure.

figuration is homogeneous as possible along the length of the cylinders (i.e., the mineral configuration can be considered transversely isotropic).

For rocks not presenting an inherent anisotropy, the failure strength is independent of the loading orientation θ . However, for highly layered rocks such as slate, schist or shale, the failure strength largely varies with θ in a ‘U’ shape with minimal strength for an orientation around $\theta \simeq 25^\circ$, and increasing strength as $\theta \rightarrow 0^\circ$ or 90° [5, 12, 8, 13, 14, 11, 15]. As shown early by Hoek in 1964, the ‘U’ shape is consistent with Griffith’s theory of brittle fracture of materials, in which the maximum stress at the tip of the crack triggers the propagation of a fissure once a critical amount of energy is added to the system. The rock microstructure is then capable of signing the failure modes and patterns. This in turn significantly affects the stress-strain relations at a macroscopic level (i.e., stiffness, hardening/softening, and strength) [16, 17].

It is important to clearly distinguish between inherent and induced anisotropies. While the first is defined here as a property of the fabric, the latter refers to anisotropies arising from that primary structure, such as the joint distribution in space. Although the anisotropies mentioned up this point are only related to geometrical properties, they can also arise from the loading configuration (i.e., stress-induced anisotropies). Indeed, a detailed description of both inherent and induced anisotropies are key elements for understanding the behavior of brittle materials, as we will show in this paper.

Improving our understanding of anisotropic geological materials will help us better address problems involving rock and grain fragmentation, such as railway ballast design [18, 19], rockfill dam design [20, 21, 22], rock tunneling processes [23, 24], mining waste dumps construction [25], surface subsidence

[26], slip stability analysis of fault gouges [27], filling rock mass discontinuities [28], the geological formation of glacial till [29], confined comminution [30, 31], weathering and environmental degradation effects [32], the failure localization in progressively deteriorated disordered structures [33], etc.

In this paper, we use bi-dimensional discrete-element modeling to study the failure strength of circular samples that have an inherent anisotropic configuration under varied loading orientation. In Sec. 2, we introduce our numerical strategy based on the contact dynamics and the bonded-cell methods, and the sample construction and testing procedures. In Sec. 3, we characterize the failure strength of two-inherent anisotropic structures showing a good agreement with experimental observations. We then analyze the failure strength variability in terms of Weibull’s statistics and failure mode evolution. Section 4 focuses on a fine description of the microstructure in terms of fabric connectivity, force transmission, and inherent and induced anisotropies. In Sec. 5, we develop a theoretical analysis that allows us to discover the microstructural origins of the crushing strength in terms of the level of inherent anisotropy and loading orientation. This analytical approach based on the granular stress tensor and its harmonic decomposition linking microstructure and the macromechanical response. Finally, we conclude with a summary and perspectives.

2. Numerical modeling

Inherently anisotropic materials are challenging to characterize given the complex and multiscale properties that minerals, grains, bonds, and fissures can present in space. Numerical approaches have proven successful at analyzing these materials because they are able to reproduce complex failure mechanisms under controlled geometries. Some of these approaches use, for example, finite-elements [34, 35], discrete-element methods with bonded bodies [36, 37, 38, 39, 40, 41], splitting or replacing mechanisms [42, 43, 44, 45], or coupled discrete-finite element strategies [46, 47, 48, 49, 50].

Among these approaches, the discrete-element method (DEM) has become increasingly popular for dealing with fragmentation due to its versatility in reproducing grain fissuring, crushing, and many experimental observations [51, 52, 53, 54]. However, some modeling strategies employ circular particles to represent grains and blocks [55, 56, 57], which does not capture the complex variability of fragments’ shapes and sizes. Other studies use a ‘replacement’ method in which bigger grains are substituted by a set of smaller

bodies once a criterion is reached [58, 43, 59], at the expense of missing mass conservation or creating local over-stresses at the replacement instant. Finally, energy consumption is not traceable when using circular bodies, or *ad-hoc* parameters are necessary to estimate the fragmentation energy. While these approaches have enabled the exploration of certain mechanisms of rock and grain failure, no clear mapping between the variability of strength, failure modes, and the microstructure has been found for inherently anisotropic materials. A correct simulation of these materials requires a model in which bodies can break into irregular and size disperse fragments while simultaneously controlling the inherent anisotropy level. As we show in the next section, these conditions can be met in 2D simulations using irregular convex polygons.

2.1. Construction of inherently anisotropic samples

We build circular samples composed of smaller bodies called *cells* using a Voronoi decomposition of a unitary circle. This procedure generates an assembly of N_{cl} adjacent cells that we ‘glue’ using a cohesive bonding law. This approach, known as the bonded-cell method (BCM), has been used in numerous studies of the mechanical behavior of crushable granular materials, both in 2D [60] and 3D [61, 62, 63].

A random Voronoi tessellation normally creates a disordered distribution of cell shapes and sizes. In order to control the cell’s geometry (and, in effect, the inherent anisotropy), we alter the initial tessellation in two steps. First, we iteratively rebuild the Voronoi tessellation using the centroids of previous tessellation seedings to produce similar cells. This approach is also called centroid tessellation [64]. Then, the cells are elongated along a given direction and an anisotropy level is estimated using the average aspect ratio of the cells $\eta = h/L$, with h and L being the average short and long dimensions, respectively. This anisotropy represents the inherent anisotropy configuration of the minerals in our model. We produced a set of samples with $\eta = [1, 6]$ in steps of 1 (see Fig. 3). Additionally, perturbations to the initial setting of the tessellation enabled us to have slightly different cell arrangements. For statistical representativeness, we built five different configurations for each value of η .

In order to give mechanical strength to the assembly of cells, we define a normal and tangential cohesion at the bonds (i.e., cell-cell interactions), C_n and C_t , respectively. C_n prevents the interactions between cells from separating due to tensile stresses, while C_t provides resistance against sliding.

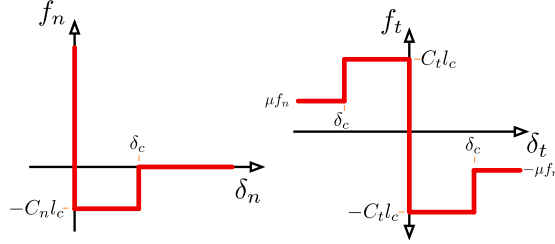


Figure 2: Interaction law for cohesive bonds between cells for the normal (left) and the tangential components (right) relative to the local framework coordinates.

We also preset a debonding distance δ_c needed to effectively break a cohesive bond. By choosing a typical value of surface energy density for silicate minerals $\gamma = 50 \text{ J/m}^2$ [65], we can then determine the separation threshold as $\delta_c = 2\gamma/C_n$, following fracture mechanics theory. Note that our model allows us to independently define the tensile and shear bonding strength, but for simplicity we set $C_n = C_t$. A detailed analysis of the combined effect of varying C_n and C_t can be found in Ref. [61].

The critical rupture energy that a bond needs to break is thus $E_c = 2\gamma l_c$, with l_c the length of the interaction. Once E_c is reached, the cohesive bond is removed, simulating a fissuring event. These fissures are considered dry frictional surfaces, with μ being the coefficient of friction that we set to 0.4 (see Fig. 2 for a schematic representation of the bonding law).

In addition, numerical studies have explored the effect of the number of cells on the failure strength of brittle materials, showing that an increased number of cells lowers the failure strength [60, 63]. However, it was recently shown that the scalability of failure strength is not simply linked to the number of cells, but more importantly to the length of bonding interactions [62, 66]. Thus, to make the tests comparable, samples must present the same potential surface energy among the different values of η despite presenting a different number of cells. So, in our tests, the samples have the same total length of bonds.

2.2. Contact dynamics

The contact dynamics (CD) method is a discrete-element approach in which rigid bodies interact via *non-smooth* laws [67, 68], i.e., impacts are transmitted on an implicit time-stepping scheme. At the end of each time-step, particles' velocities and contact forces can therefore be simultaneously

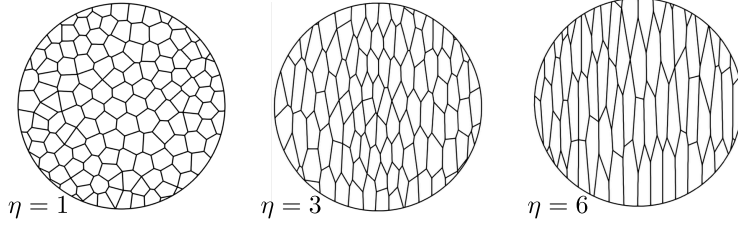


Figure 3: Samples presenting increasing average cell aspect ratio η . We varied η from (a) 1 up to (f) 6 in steps of 1.

computed without requiring force-overlapping laws (i.e., no regularization of the contact law is needed). This allows the CD method to be unconditionally stable and capable of employing larger time-steps than in alternative *smooth* approaches. For details on implementation of the contact dynamics method, see Refs. [69, 70].

In two-dimensional simulations, three main interactions can occur between convex bodies: vertex-vertex, vertex-edge, edge-edge (see Fig. 4). Vertex-vertex interactions are rare and unstable, so they are discarded from the computation and analysis. For edge-edge interactions, it is necessary to consider two contact points to correctly resolve the contact mechanics; however, only the resultant force is important, rendering the loci of the two contact points irrelevant. For the interaction detection and classification, we use the *shadow-overlap method* [71], which creates a separating plane between two touching bodies via an iterative procedure. Updated body positions, velocities, and interaction forces are governed by the equations of motion and the cohesive bonding law we previously defined.

Finally, it is worth mentioning that our simulations were performed using the CD method on the free and open-source platform LMGC90 [72, 73].

2.3. Test procedures

Samples are initially set matching the loading orientation with the cells' preferred direction, so $\theta = 0^\circ$. Then, we apply a gradually increasing vertical force F using rigid platens up to the failure. To avoid dynamic perturbations during loading, we make sure that, over a time-step, a load increment is very small before $C_n d$, with d being the diameter of the samples. We systematically vary θ in the range $[0^\circ, 90^\circ]$ in steps of 5° , i.e., 18 different orientations (see Fig. 1). Finally, we test five different configurations of η for each one of the angles for statistical representativeness. Videos of the tests can be

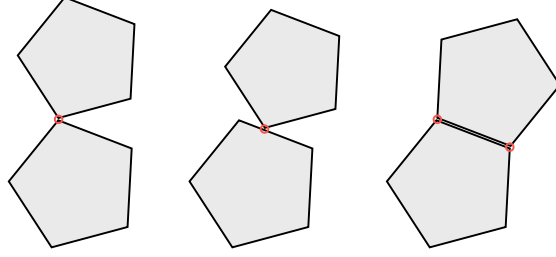


Figure 4: Different interaction types between convex polygons: (left) vertex-vertex, (center) vertex-edge, and (right) edge-edge.

found at the following link https://youtu.be/N66c_4crw1M. We present the averaged results of the total 540 simulations we performed.

3. Macroscopic observations

3.1. Failure strength

Our samples are able to reproduce a brittle material behavior by supporting a load that gradually increases up to a critical value that triggers the collapse of the assembly (see Fig. 5(a)). The critical force at failure F_c allows us to characterize strength using the vertical stress at failure, defined as

$$\sigma_{yy} = \frac{F_c}{d}. \quad (1)$$

Figure 5(b) summarizes the average values for σ_{yy} found in our tests as a function of θ and the inherent anisotropy η . Under the same loading rates, the internal cohesion is a natural scaling parameter for these systems. So, we plot σ_{yy} normalized by C_n .

Note that for the case $\eta = 1$, in which the cells do not present any characteristic orientation, the strength is independent of the angle θ . For the anisotropic configurations where $\eta > 1$, the strength remains relatively similar for loading orientations below $\theta \simeq 70^\circ$, but always underneath the values found for the case $\eta = 1$. Beyond $\theta \simeq 75^\circ$, there is an important gain in strength, which seems accentuated as η increases. Finally, a maximum failure strength is found for loading orientation perpendicular to the layering of the cells (i.e., $\theta = 90^\circ$).

As previously mentioned, experimental observations have systematically highlighted the ‘U’ shape displayed in Fig. 5(b), with a critical loading orientation θ_c exhibiting the minimal strength. Simple stress considerations can

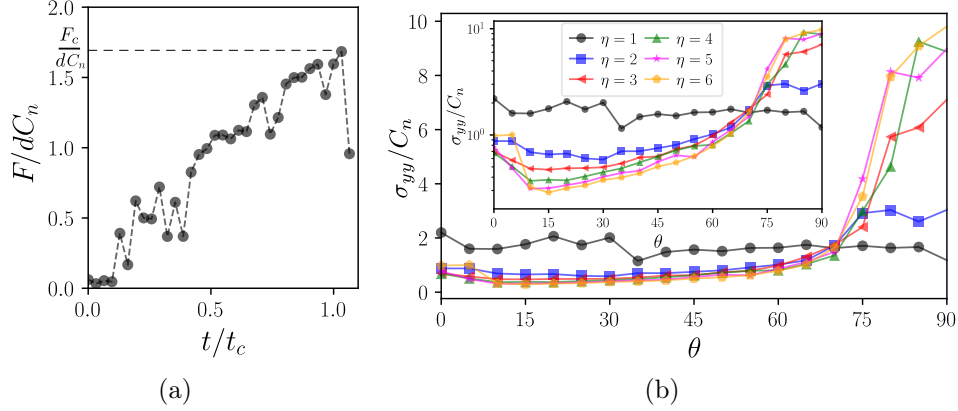


Figure 5: (a) Typical evolution of the reaction force F on the loading plate as a function of the simulation time normalized by the time at failure t_c . (b) Strength σ_{yy} normalized by the normal bonding cohesion C_n as a function of the relative loading orientation θ and different levels of inherent anisotropy η . In the inset, we present the same data in lin-log scale.

predict that critical orientation as $\cos 2\theta_c = (1 - \kappa)/2(1 + \kappa)$, with $\kappa = \sigma_1/\sigma_2$ being the ratio between the major and minor principal stresses on the sample [1]. For the diametral point load, in which $\sigma_2 = 0$, we can easily deduce that $\theta_c = 30^\circ$. Nonetheless, in our tests θ_c varies with η from $\simeq 30^\circ$ for $\eta = 2$, to $\simeq 15^\circ$ for higher values of η (see inset of Fig. 5(b)). These observations show that our numerical experiments are in good agreement with experimental testing and analysis, despite the fact that the ‘U’ shape in our results is more subtle than what is reported in literature. We have to remark, nonetheless, that larger variations of the failure strength with angle θ can be found once a confining pressure is applied to the sample [3]. In addition, some of the tests on inherently anisotropic rocks are performed by loading the circular faces of the rock cores. It has been shown, however, that diametrical point load on cylindrical samples produces more subtle variations of failure strength [9]. The increasing disagreement in θ_c with respect to the theoretical estimation also suggests that the inherent anisotropy deeply modifies the stress configuration within the samples.

For the case without inherent anisotropy, we can follow classical rock mechanics testing and use the maximum tensile stress criterion to characterize the strength of our samples [74, 75]. So the expression $\sigma_c = 2F_c/\pi d$ allows one to deduce the maximum tensile stress at the center of the circular sample. Using that equation, we find that, on average, $\sigma_c/C_n \simeq 1$. This result allows

us to make two important observations: 1) our model correctly scales the internal material strength (C_n) to the macroscale, and 2) it can be correctly assumed that for a non-anisotropic brittle structure, the tensile stresses are indeed triggering the failure. However, experimental testing characterizing inherently anisotropic materials should be aware that the tensile stresses are not necessarily at the origin of failure.

3.2. Statistical variability of strength

To better understand the variability of failure strength, we analyze our results in terms of ‘survival’ using the Weibull probability distribution. This approach assumes that a sample’s probability of not presenting failure P_s (i.e., the survival) depends on the applied stress σ as

$$P_s = \exp \left\{ - \left(\frac{\sigma}{\sigma_0} \right)^m \right\}, \quad (2)$$

with σ_0 being a reference stress for which $P_s = 1/e \simeq 37\%$. The exponent m is known as the Weibull modulus and is associated with the sharpness of the probability distribution. As m increases, so does the slope of the distribution, meaning that the failure strength is focused on a given value. Conversely, as m decreases, the stress range within which the particle may break broadens.

Figure 6 presents the survival probability distribution P_s as a function of the applied stress and the different values of η , combining all results by θ . As expected, the stress range σ within which we can expect failure considerably increases with η . The dashed lines correspond to the fitting of Eq. (2) by finding m and σ_0 with a least-squares minimization. The inset on the same figure presents the values found for the Weibull modulus m as a function of η . Typical values for parameter m for silicate materials are found in the range $[1.5, 4]$ [76, 19]. We observe that for microstructures with $\eta = 1$, m reaches a value of $\simeq 2.5$ and then smoothly decreases as values of inherent anisotropy grow. It is remarkable that our experiments satisfactorily reproduce the Weibull modulus for brittle silicate materials despite the strong variation of the cell’s configuration, the simplicity of our model, and the fact that we are not able to store elastic energy/deformation in the bulk of the cells. Typical values for parameter m for silicate-rich materials have been found, for instance, in the range $m \in [1.16, 1.93]$ for silica sand [77], $m \in [1.23, 3.04]$ [78] for different silica sands from Japan, $m \in [3.34, 3.44]$ [79] for limestone sand,

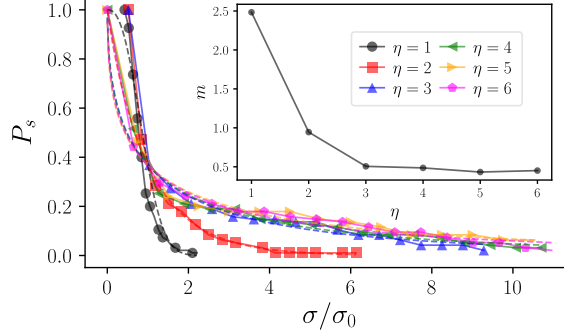


Figure 6: Probability of survival P_s as a function of the applied stress σ for each value of η and all values of θ combined. The dashed lines correspond to the fit of Eq. (2) to the data. In the inset, we present the corresponding value of the Weibull modulus for each fit of the Weibull distribution.

and $m \in [1.26, 2.52]$ for calcareous and quartzite shale aggregate rocks [21], agreeing with our results. Although our modeling strategy was developed targeting the brittle behavior of soil grains and rocks, higher values of m can be obtained for different materials by adjusting parameters γ , C_n , and C_t .

If we combine all values of failure strength - not distinguishing between η and θ - we find that $m \simeq 1.5$, which falls within a typical range of values for rocks or grains that are not necessarily anisotropic. This observation suggests that laboratory tests in which no special attention is given to the degree of inherent anisotropy or loading orientation can gather a wide variety of material characteristics. Such a simplified approach could thus be misleading and limit the predictability of the material failure strength.

3.3. Macroscopic failure modes and energy consumption

Figure 7 presents the fissuring paths for some of the samples with $\eta = 2$ and varying loading orientation θ . When $\theta = 0^\circ$, the failure is roughly vertical, matching the loading orientation. The failure mechanism is similar when $\theta = 90^\circ$, although the zones in contact with the platens show more damage. In these two cases, we can infer that tensile stresses are the source of fissuring because many interactions are debonded orthogonally to the loading direction. However, when $\theta = 30^\circ$ and 60° , the failure mode is different. The fissuring is diagonal to the loading, which suggests that shearing is the preferred fissuring mode. These observations are in agreement with physical experiments [9, 50, 10] and help to justify the substantial drop in failure strength σ_{yy}/C_n for inherently anisotropic structures.

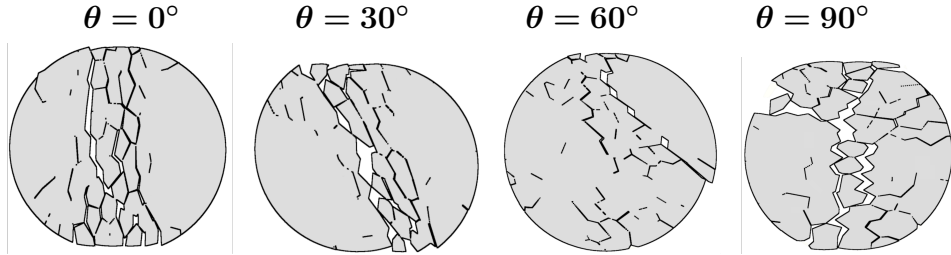


Figure 7: Evolution of the failure mechanism as the loading orientation increases from $\theta = 0^\circ$ up to $\theta = 90^\circ$ for the sample with inherent anisotropy $\eta = 2$.

Note that this observation about the macroscopic failure modes is descriptive. A quantitative assessment of the energy consumption shows that all the samples consume roughly the same amounts of fragmentation energy independently of θ and η using the same Bonded-Cell Method [66]. This is a very counterintuitive phenomenon that has been scarcely studied or validated in physical experiments. A recent work [] using notched rock cores has established a dependency between the fragmentation energy and the bedding angle θ , although different test conditions and variability of results call for further experimental validations. While our numerical model is indeed simple and does not consider the elastic deformation the cells can undergo, the BCM modeling let us deduce that the total length of cohesive bonds is the central parameter controlling the energy consumption. Thus, the variability in failure strength is strongly linked to microstructural elements rather than to mechanisms splitting failures between tensile and shearing modes.

4. Microstructural analysis

As previously mentioned, rock microstructure is often related to mineral or grain size and shape distribution, joint spacing/density, fissuring, and etc. All of these geometrical characteristics clearly affect the failure strength. However, the microstructure cannot only be reduced to its geometrical aspects. Accounting for the connectivity between cells and the force transmission are key elements behind the macroscopic mechanical behavior.

In order to do this, we first need to define a framework of analysis. We have two possibilities when dealing with adjacent cells. First, the *interaction* frame in which the bond forces are defined as $\mathbf{f} = f_n \mathbf{n} + f_t \mathbf{t}$, with \mathbf{n} being the normal unit vector perpendicular to the contact line, and \mathbf{t} being the tangential unit vector.

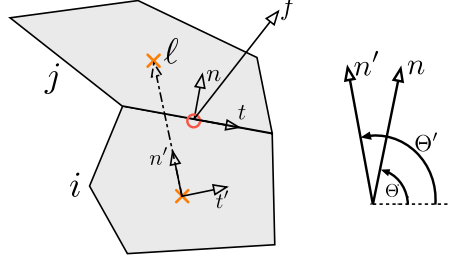


Figure 8: Schematic representation of the local frames created between two irregular cells i and j . Unitary vectors \mathbf{n} and \mathbf{t} are linked to the bond, while \mathbf{n}' and \mathbf{t}' are defined upon the branch vector. Note that angles Θ and Θ' are the orientation of \mathbf{n} and \mathbf{n}' , respectively, measured counterclockwise from the horizontal.

We can also define the inter-center vectors between cells, also called *branch vectors*, as $\boldsymbol{\ell} = \ell_n \mathbf{n} + \ell_t \mathbf{t}$, with ℓ_n and ℓ_t being the normal and tangential components. These branches let us define a second frame in which the unit vector \mathbf{n}' is defined along $\boldsymbol{\ell}$, and \mathbf{t}' is the tangential unit vector (see Fig. 8) [80]. In this frame, the forces between the cells are written as $\mathbf{f} = f'_n \mathbf{n}' + f'_t \mathbf{t}'$, with f'_n and f'_t - the radial and ortho-radial forces, respectively - acting between the centers of the cells. Finally, the branch in this frame is simply written as $\boldsymbol{\ell} = \ell \mathbf{n}'$, with ℓ being the length of the branch vector. For convenience, we used the branch frame for the following microstructural analysis.

As an illustration, Fig. 9 (top) presents the branch network and the force network (bottom) with lines whose thickness is proportional to the intensity of the force at the interactions. A visual inspection shows how the geometry of the cells dramatically modifies both networks. As η increases, the branch network becomes more irregular and the force chains more diffuse within the volume.

4.1. Geometrical description

4.1.1. Connectivity

We can characterize the connectivity between cells by using the coordination number Z . This parameter shows the average number of neighboring interactions per cell as $Z = 2N_c/N_{cl}$, with N_c being the number of bonds between cells and N_{cl} the number of cells. There is, however, a subtle difference in coordination number between the intact state (i.e., at the beginning of the loading) and the coordination number we are able to compute instants

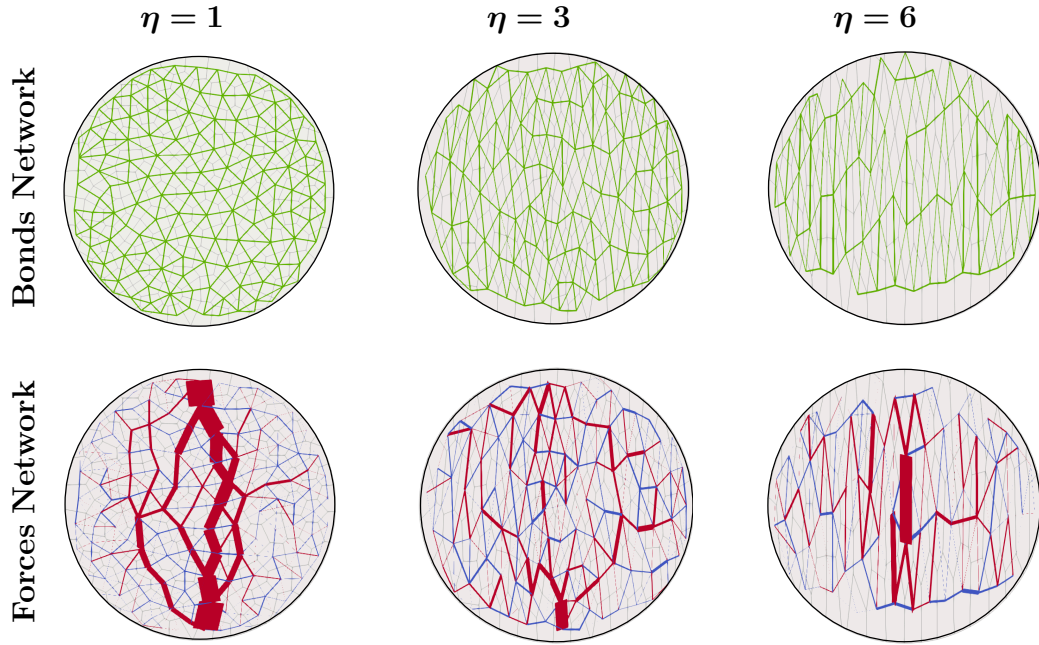


Figure 9: (Top) Networks created by bonded adjacent cells for $\eta = 1, 3$ and 6 displayed with lines between the center of mass of the corresponding cells. (Bottom) Force networks between bonded cells. The thickness of the lines is proportional to the force intensity. Traction forces are displayed in blue and compression forces in red. These screenshots are taken for cases in which the loading orientation is $\theta = 0$.

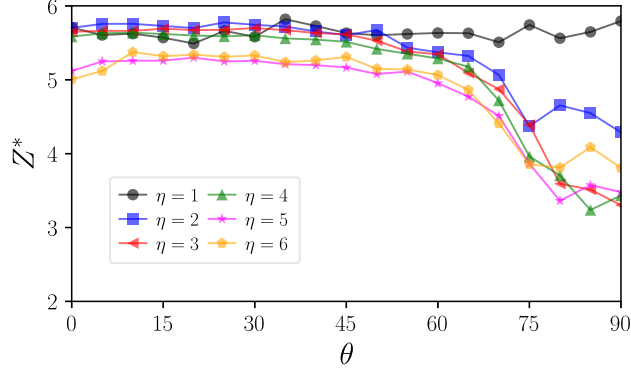


Figure 10: Evolution of the coordination number at the onset of failure Z^* as a function of the loading orientation θ and the inherent anisotropy η .

before failure. Both values differ, as fissuring removes cohesive bonds previously capable of bearing force. We characterize the onset of failure as the state bearing σ_{yy} , so let us consider the cohesive bonds at the onset of failure N_c^* as the effective number of interactions, so $Z^* = 2N_c^*/N_{cl}$.

Figure 10 presents the averaged coordination number at the onset of failure as a function of η and θ . We observe that the connectivity decreases as θ and η increase. In other words, Z^* varies conversely to σ_{yy} showing that inherently anisotropic materials can bear larger stresses despite the fact that cells are less connected. The evolution of Z^* provides a counterintuitive picture of the effect of θ and η on the microstructural properties at failure. However, as previously shown in Fig. 8, the branch and force networks also carry a strong anisotropic character that calls for a higher-order analysis accounting for their distribution in space.

4.1.2. Branch orientations

We can define the density probability distribution P_c of branch vector orientations as

$$P_c(\Theta') = \frac{N_c^*(\Theta')}{N_c^*} \quad (3)$$

with $N_c^*(\Theta')$ being the number of branches pointing at angle Θ' at the onset of failure. The inset of Fig. 11(b) presents the angular distributions $P_c(\Theta')$ with symbols for three different values of inherent anisotropy and loading orientations $\theta = 0^\circ$ and $\theta = 90^\circ$. We can see that when $\eta = 1$ the distribution remains almost circular, highlighting the fact that the bond

network is nearly isotropic and independent of the assembly's rotation. Conversely, the distributions for $\eta > 1$ present preferential orientations matching the preferred orientation of the cells.

These angular distributions can also be described using truncated Fourier series, as

$$P_c(\Theta') = \frac{1}{2\pi} \{1 + a'_c \cos 2(\Theta' - \Theta'_c)\}, \quad (4)$$

with Θ'_c being the preferential orientation of the distribution and a'_c its anisotropy level, i.e., the branch vector orientation anisotropy. Note that $a'_c = 0$ means a circular distribution P_c , in which bonds are equally presented in all orientations Θ' . Conversely, as a'_c increases, more bonds present a preferential orientation in space. Although we could fit Eq. (4) to our measures to find a'_c and Θ'_c , we prefer to use the *fabric* tensor defined as [81]

$$\mathbf{F}_{ij} = \int_0^\pi P_c(\Theta') n'_i(\Theta') n'_j(\Theta') d\Theta', \quad (5)$$

with $\mathbf{n}' = \{\cos \Theta', \sin \Theta'\}$. Equation (5) lets us define the anisotropy of branch orientations as $a'_c = 2(F_1 - F_2)$, with $F_1 > F_2$ being the eigenvalues of \mathbf{F} . The major principal direction of the fabric tensor is $\Theta'_c = 1/2 \arctan\{2F_{xy}/(F_{xx} - F_{yy})\}$, with F_{xx} and F_{yy} being the components in the diagonal of \mathbf{F} , and F_{xy} the component off the diagonal. Figure 11 presents the corresponding values of preferential branch orientation and anisotropy as a function of η and θ .

We can observe that a'_c is close to zero for $\eta = 1$, exposing the isotropic character of the branch network and its independence before θ . For $\eta > 1$, a'_c can reach larger values as high as $\simeq 1.1$ for $\eta = 6$. There is also a slight drop in a'_c occurring for values of $\theta > 70^\circ$. This phenomenon, combined with the drop of Z^* we observed before, suggests that contacts are mostly lost in the minor orientation of the fabric tensor as η increases.

In Fig. 11(b), we present the evolution of Θ'_c as a function of the loading orientation θ . For $\eta = 1$, Θ'_c is irrelevant given that $a'_c \simeq 0$, so it is omitted from the plot. But as soon as $\eta > 1$, Θ'_c decreases as $\pi/2 - \theta$ which matches the cells' orientation.

Along with P_c , we can also characterize the angular branch length distribution $\langle \ell \rangle(\Theta')$. This distribution can be computed as a function of Θ' as

$$\langle \ell \rangle(\Theta') = \frac{1}{N_c^*(\Theta')} \sum_{c \in \delta\Theta'} \ell^c, \quad (6)$$

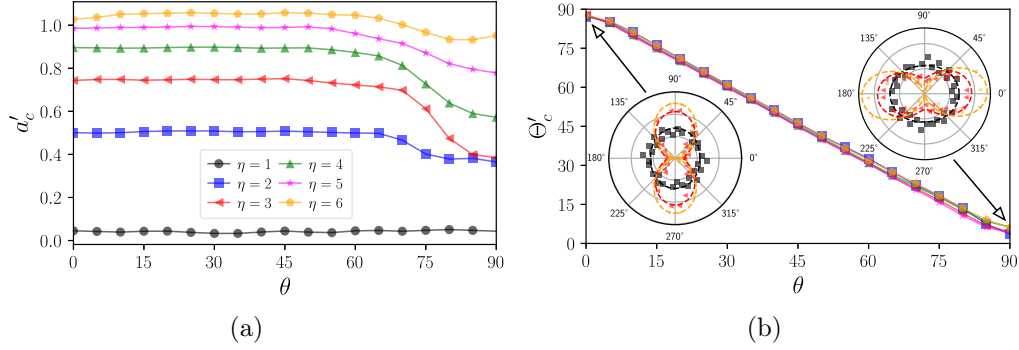


Figure 11: Bond orientation anisotropy a'_c (a) and the preferential orientation Θ'_c (b) for different inherent anisotropy levels η and loading orientations θ . In the inset: probability of branch orientations $P_c(\Theta')$ shown with symbols for three values of inherent anisotropy η and loading orientation $\theta = 0^\circ$ and $\theta = 90^\circ$. The dashed lines are the fitting curves using Eq. (4).

with ℓ_c being the length of the branches pointing at small intervals of angular orientation $\delta\Theta'$. The inset in Fig. 12(b) presents these angular distributions for loading orientations $\theta = 0^\circ$ and $\theta = 90^\circ$, and three values of η . These angular distributions for branch lengths closely follow the trends previously seen for $P_c(\Theta')$.

As with branch orientations, the angular evolution of branch lengths can be described using the expression

$$\langle \ell \rangle(\Theta') = \langle \ell \rangle \{1 + a'_\ell \cos 2(\Theta' - \Theta'_\ell)\}, \quad (7)$$

with Θ'_ℓ being the preferential orientation, and a'_ℓ the level of anisotropy. In the insets of Fig. 12(b), we show that the branch length distributions become more anisotropic as η increases, and that the longest branches predominately point in the same direction as the cells are pointing.

To find the branch length anisotropy, it is convenient to build the *branch tensor*, which is defined in an integral form as [81]

$$H_{ij}^\ell = \int_0^\pi \langle \ell \rangle(\Theta') n'_i(\Theta') n'_j(\Theta') d\Theta'. \quad (8)$$

Note that this integral is computed in the range $[0, \pi]$ given the periodic evolution of the angular distributions in that interval. We can then compute the branch length anisotropy as $a'_\ell = 2(H_1^\ell - H_2^\ell)/(H_1^\ell + H_2^\ell)$, with H_1^ℓ and

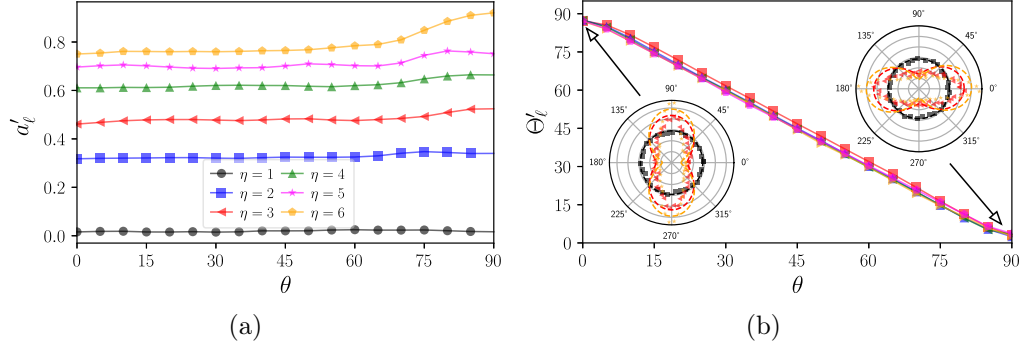


Figure 12: Evolution of the normal branch length anisotropy (a) and its preferential angular orientation (b) as a function of the loading orientation and values of inherent anisotropy η . In the inset: angular distribution branch lengths for some values of inherent anisotropy η for loading orientations 0° and 90° . We also present Eq. (7), fitting the angular branch length distributions with dashed lines.

H_2^ℓ being the eigenvalues of the tensor, so $H_1^\ell > H_2^\ell$. The same construction allows us to compute Θ'_ℓ as the major principal orientation of H^ℓ using the same approach as with the fabric tensor. In the inset of Fig. 12(b), we present Eq. (7) with dashed lines using the values extracted from the tensors above, and nicely fitting the angular distributions. We deliberately omitted the evolution of $\langle \ell \rangle(\Theta')$ for $\eta = 1$ since the corresponding values for a'_ℓ are negligible.

Figures 12(a) and 12(b) gather the results for the branch anisotropies a'_ℓ and preferred orientations Θ'_ℓ as a function of the loading orientation θ and the levels of inherent anisotropy η . They show that the branch length anisotropy increases with η from $a'_\ell \simeq 0$ for $\eta = 1$, up to $a'_\ell \simeq 0.7$ for $\eta = 6$. In all of the cases, these anisotropies present only minor variations with the loading orientation θ . We can then say that the variation of the preferred orientation for branch lengths evolves roughly as $\pi/2 - \theta$, similarly to $P_c(\Theta')$.

The large variations of geometrical anisotropies that we observed are induced by the inherent anisotropy of the cells - and, furthermore, η is likely also inducing force transmission heterogeneities within the samples. In order to investigate this, we focus next on the interaction forces between cells.

4.1.3. Force orientations

Similarly to the analysis undertaken for branches, we can analyze the interaction forces between cells by using the angular distribution of radial

and ortho-radial forces f'_n and f'_t , respectively. These angular distributions can be computed as

$$\langle f'_n \rangle(\Theta') = \frac{1}{N_c(\Theta')} \sum_{c \in \delta\Theta'} f'_n, \quad \text{and} \quad (9)$$

$$\langle f'_t \rangle(\Theta') = \frac{1}{N_c(\Theta')} \sum_{c \in \delta\Theta'} f'_t. \quad (10)$$

In the insets of Fig. 13(b), we present the angular distribution $\langle f'_n \rangle(\Theta')$ for loading orientation $\theta = 45^\circ$ which shows the misalignment of the largest forces with respect to the vertical (i.e., the loading orientation). In the insets of Fig. 13(d), we present the distributions of ortho-radial forces for $\theta = 0^\circ$ and $\theta = 90^\circ$, highlighting how widely these distributions vary as the assembly rotates. Regardless, these angular distributions remain periodic and smooth enough to fit Fourier series for their characterization. We can thus describe the angular variation of forces as

$$\langle f'_n \rangle(\Theta') = \langle f'_n \rangle \left\{ 1 + a'_{f_n} \cos 2(\Theta' - \Theta'_{f_n}) \right\}, \quad \text{and} \quad (11)$$

$$\langle f'_t \rangle(\Theta') = \langle f'_t \rangle \left\{ -a'_{f_t} \sin 2(\Theta' - \Theta'_{f_t}) \right\}, \quad (12)$$

with a'_{f_n} and a'_{f_t} being the level of anisotropy for each distribution, and Θ'_{f_n} and Θ'_{f_t} the respective preferential orientations. For convenience, we build *force tensors* that allow us to easily compute the anisotropies and main orientation of each distribution as

$$H_{ij}^{f'_n} = \int_0^\pi \langle f'_n \rangle(\Theta') n'_i(\Theta') n_j(\Theta') d\Theta', \quad \text{and} \quad (13)$$

$$H_{ij}^{f'_t} = \int_0^\pi \langle f'_t \rangle(\Theta') n_i(\Theta') t_j(\Theta') d\Theta'. \quad (14)$$

This lets us compute the levels of force anisotropy as $a'_{f_n} = 2 \left(H_1^{f'_n} - H_2^{f'_n} \right) / \left(H_1^{f'_n} + H_2^{f'_n} \right)$ for the radial forces and $a'_{f_t} = 2 \left(H_1^{f'_t} - H_2^{f'_t} \right) / \left(H_1^{f'_n} + H_2^{f'_n} \right)$ for the ortho-radial forces, where H_1^α and H_2^α are the eigenvalues of each one of the tensors. Note that $H_1^\alpha > H_2^\alpha$, and α stands for either the radial or ortho-radial components of the forces. It is worth mentioning that $\text{tr} \left(H^{f'_n} \right) = \langle f'_n \rangle$, i.e., the average radial force, and $\text{tr} \left(H^{f'_t} \right) = 0$ by equilibrium of force moments over the cells.

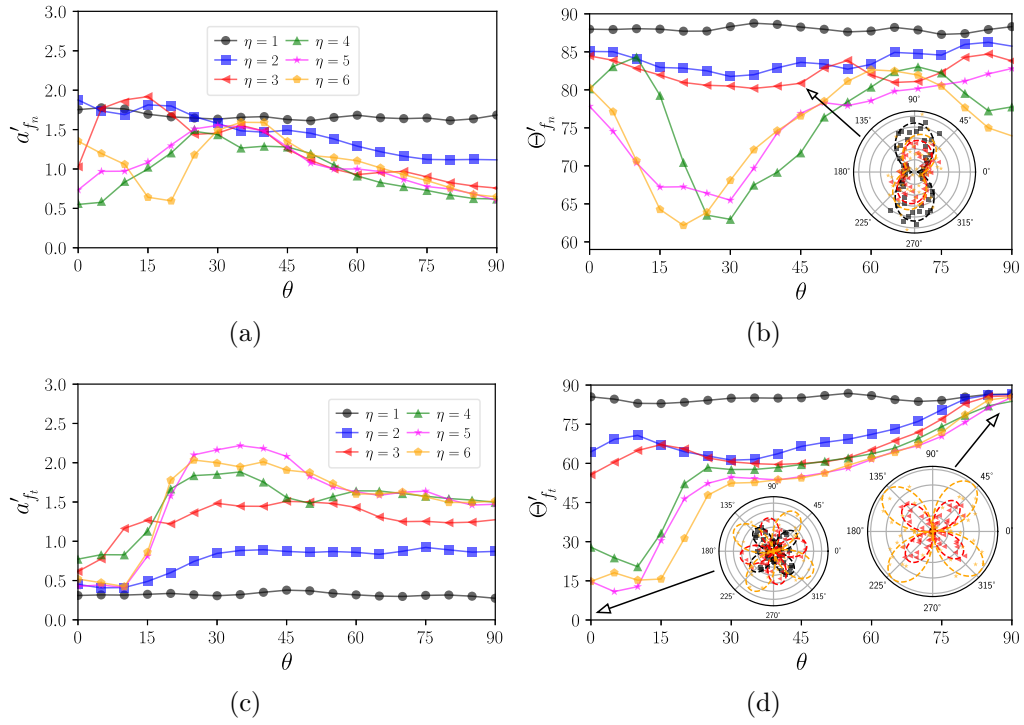


Figure 13: Evolution of normal (top) and tangential (bottom) force anisotropies (left) and the preferential orientation of their respective angular distribution (right) for different values of inherent anisotropy η and loading orientation θ .

Figures 13(a) and 13(b) display the radial force anisotropies and their preferential orientations for the different levels of inherent anisotropy η and loading orientation θ . In the case of $\eta = 1$, we can observe that $a'_{f_n} \simeq 1.8$ independently of the loading orientation. Then, a'_{f_n} progressively increases with η in the range $\theta \simeq [0^\circ, 30^\circ]$. After the loading orientation $\theta \simeq 30^\circ$, the radial force anisotropy presents a decreasing trend relatively similar among the different values of $\eta > 1$. The preferred orientations of these forces show larger variations with θ ; a behavior that seems amplified with η . Also, note that for Θ'_{f_n} a minimum value systematically appears around $\simeq 20^\circ$.

For ortho-radial forces, Figs. 13(c) and 13(d) present the evolution of the level of anisotropy and preferential orientations as a function of η and θ . In this case, we observe a continuous increase of a'_{f_t} as a function of η from loading orientations $\theta = 0^\circ$ to $\theta \simeq 45^\circ$. Beyond that loading orientation, the ortho-radial force anisotropy reaches a plateau and barely varies with θ . For the orientations Θ'_{f_t} , we can see a variation that becomes more important as the level of inherent anisotropy increases. Although we might have expected a joint evolution of the preferential radial and ortho-radial forces' orientations, these figures show that a non-evident trade-off of force anisotropies occurs for highly anisotropic materials. This fact is, of course, emphasized by the point loading configuration which signs the force transmission at bonds.

5. Scaling up the strength from the microstructure

5.1. Microstructural contributions to the stress tensor

The previous microstructural parameters - concerning bonds, branches, and forces - must act together to produce the macroscopic failure strength we initially measured. This mapping between the micro and macro scales is especially challenging because of the varying shapes and sizes of the cells and the fact that the different microstructural tensors are strongly misaligned and evolving with θ .

In order to reconcile the micro and macro scales, let us consider the granular stress tensor as [82, 83]

$$\sigma_{ij} = \frac{1}{V} \sum_{\forall c} f_i^c \ell_j^c, \quad (15)$$

where V is the volume of the sample, and the sum includes the dyadic product of the force \mathbf{f} and branch $\boldsymbol{\ell}$ vectors for all interactions c . Supposing that the

distribution of forces and branches is uncorrelated (which is verified in our simulations), we can rewrite the stress tensor in terms of angular distributions on the frame $\{\mathbf{n}', \mathbf{t}'\}$ as [81]

$$\sigma_{ij} = n_c \int_0^\pi \{ \langle f'_n \rangle(\Theta') n'_i(\Theta') - \langle f'_t \rangle(\Theta') t'_i(\Theta') \} \langle \ell \rangle(\Theta') n'_j(\Theta') P_c(\Theta') d\Theta', \quad (16)$$

with n_c being the bond number density defined as $N_c/V = Z/(2\langle V_{cl} \rangle)$, where $\langle V_{cl} \rangle$ is the average volume per cell. Note that we can also write $\langle V_{cl} \rangle = (\pi/4)\langle d_{cl} \rangle^2$, with $\langle d_{cl} \rangle$ being the equivalent average diameter of the cells. When we replace Eqs. (4), (7), and (11) in the previous expression, focus only on the vertical component of the tensor (i.e., σ_{yy}), and integrate over the interval $[0, \pi]$, we find a microstructural definition of the vertical stress at the onset of failure as

$$\sigma_{yy}^{th} = \frac{Z\langle f'_n \rangle\langle \ell \rangle}{\pi\langle d_{cl} \rangle^2} \left\{ 1 - \frac{1}{2} \sum a'_k \cos 2(\Theta'_k) + \frac{1}{2} \sum a'_l a'_m \cos 2(\Theta'_m - \Theta'_l) + \mathcal{O} \right\}. \quad (17)$$

The term in brackets shows the contributions of the different anisotropies to the strength. In that term, the first sum runs in the set $a'_k \in \{a'_c, a'_\ell, a'_{f_n}, a'_{f_t}\}$, and in the respective values for Θ'_k . The second sum is a product of anisotropies in which the combinations of indices l and m belong, respectively, to the set $\{a'_{f_n} a'_\ell, a'_{f_n} a'_c, a'_\ell a'_c\}$, with the respective angles for Θ'_m and Θ'_l . The higher-order term \mathcal{O} involves triple products of anisotropies and is purposely neglected for the sake of simplicity. Also note that we added the superscript ‘*th*’ to emphasize that this value of strength results from the theoretical decomposition of the stress tensor. For simplicity, the term related to the anisotropies is henceforth written as \mathcal{A} .

Equation (17) illuminates the fact that non-trivial microstructural compensations occur between 1) the different anisotropy levels, 2) the preferred orientations of angular distributions, and 3) geometrical and mechanical features. In addition, the choice of the branch frame $\{\mathbf{n}', \mathbf{t}'\}$ instead of the bond frame $\{\mathbf{n}, \mathbf{t}\}$ is deliberate because it allowed us to reduce the number of anisotropies and the number of terms involved in \mathcal{A} [80].

In Fig. 14, we summarize the evolution of the different parameters involved in \mathcal{A} for single and double anisotropies. On the one hand, we see that the geometrical anisotropies related to the branch orientation a'_c and branch lengths a'_ℓ smoothly decrease as a function of the loading orientation θ . On the other, the anisotropies related to the force transmission a'_{f_n} and

a'_{ft} have a highly non-linear evolution with θ . For angles between $\theta = 0^\circ$ and $\theta = 30^\circ$, the radial force anisotropy increases but then finds a relatively steady value for larger loading orientations. For angles greater than $\theta \simeq 45^\circ$, the ortho-radial anisotropy increases strongly as a function of θ . For the terms involving the product of anisotropies, the trends are all quite similar and not negligible in contribution.

At the bottom of Fig. 14, we see how all of these anisotropies add up. Given the strong variation of all the anisotropies and preferential orientations, it is notable that the term \mathcal{A} ends up fluctuating around the case $\eta = 1$. This is clearly a mechanism involving direct compensations between geometrical microstructural characteristics and the force transmission at bonds. This phenomenon - in which the term \mathcal{A} lies close to one - shows that the strong variation of the macroscopic failure strength must lie on the parameters $Z\langle f'_n \rangle \langle \ell \rangle$ of the microstructural decomposition of stresses. Note that a version of Eq. (17) that neglects the term \mathcal{A} has been used many times before for conglomerates or granular assemblies in which particles are of similar size and shape [84, 85, 86]. Nonetheless, as we just observed, \mathcal{A} cannot be neglected for elongated bodies.

In Fig. 15(a), we see the evolution of the average branch length at the onset of failure as a function of the inherent anisotropy and the loading orientation, which shows a gradual drop as the loading becomes perpendicular to the layering. Such a variation is accentuated as η grows. In Fig. 15(b), we present the evolution of the average radial force $\langle f'_n \rangle$, which is normalized by the internal cohesion and the average cell equivalent diameter. This curve varies widely and, indeed, carries most of the shape of the macroscopic failure strength.

These observations allow us to conclude that the microstructural mechanisms producing the increase of failure strength with θ are related to the rise of radial forces, the drop of average branch length and coordination number Z , and the complex compensations occurring within the term \mathcal{A} .

Finally, in Fig. 16, we plot σ_{yy}^{th} nicely reproducing the macroscopic vertical failure stress measured in Sec. 3. It is remarkable how the approach of decomposition of the granular stress tensor in terms of angular distributions, in spite of the large variability of anisotropies and preferred orientations for each distribution, is capable of providing these set of satisfactorily good predictions for the failure strength. The small differences between the measure and the decomposition are linked to the higher-order terms that were neglected in Eq. (17). Thus, based on a fine description of the phenomena

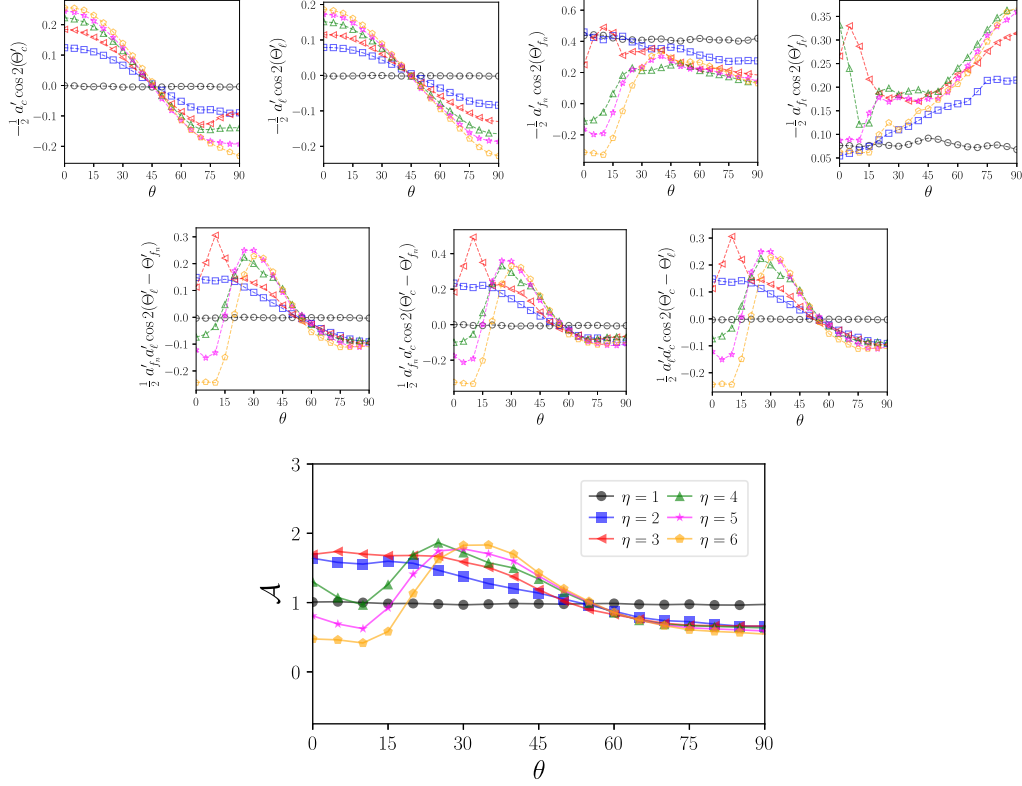


Figure 14: Evolution of the terms in Eq. (17) related to single anisotropies (first row) and double anisotropies (second row). We also present the sum of these different parameters in the term \mathcal{A} (bottom).

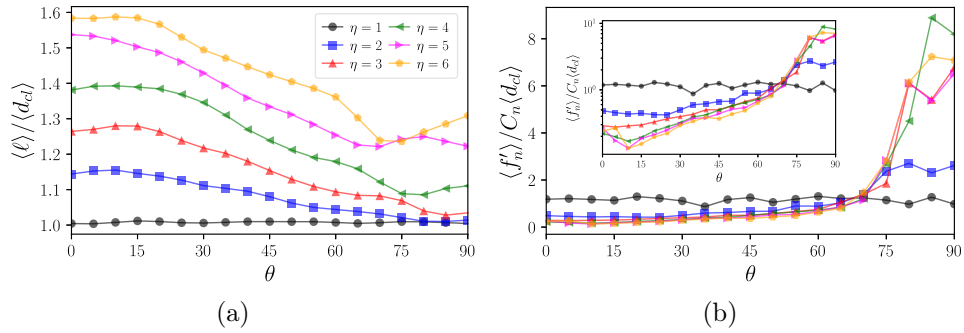


Figure 15: (a) Evolution of the average branch length as a function of η and θ . (b) Evolution of the radial average force as a function of η and θ . In the inset: the same data in lin-log scale.

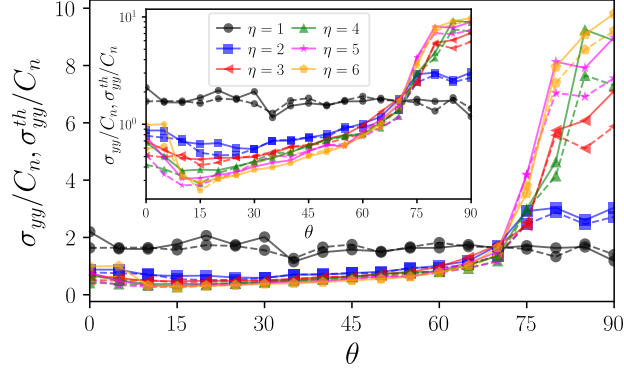


Figure 16: Failure strength measure through the wall forces just as in Fig. 5(b) (solid lines), and the same strength found using the microstructural decomposition of the stress tensor using Eq. (1) (dashed lines).

at bonds and mineral organization in space, our micromechanical description proves capable of describing and scaling up the macroscopic behavior we observe in laboratory.

6. Summary

We developed a series of numerical tests to study the failure strength of brittle materials reminiscent of schists, slates, shales, etc, whose components have a preferential orientation, i.e., an inherent anisotropy. Using a bi-dimensional discrete-element method, we built samples in which we could control the degree of inherent anisotropy by using a modified Voronoi tessellation. This approach allowed us to generate a set of subdivisions (the tessellation) of adjacent irregular polygons that we called cells. The common edges between cells interacted via cohesive bonds, enabling us to control both the failure strength and the cumulated surface energy necessary to produce fissuring. We then measured the macroscopic failure strength by applying a diametrical point load onto circular samples up to breakage. The failure strength turned out to be strongly affected by the layering orientation with respect to the loading direction θ . As observed in many experimental tests, the failure strength in our numerical tests evolved in a parabolic ‘ U ’ shape, with a minimum value around a loading orientation of $\theta \simeq 25^\circ$.

We also analyzed the variability of the failure strength using the Weibull survival probability, concluding that mixing several anisotropic configurations and loading orientations may lead to misleading conclusions upon the

average failure strength and data scatter. This means that experimental testing must consider the microstructure of samples to avoid a misinterpretation of the strength of anisotropic brittle materials.

Finally, we performed a thorough characterization of geometrical properties of the cells' assemblies and force transmission mechanisms by means of the fabric, branch, and force tensors, as well as an approximation of their angular distributions using Fourier series. Exploiting the definition of the granular stress tensor in terms of angular contributions, we were able to find the microstructural elements that explain the variability of strength at the macroscopic scale. This was not a straightforward task. The strong geometrical and force anisotropies we found - as well as the misalignment of the different tensors - prompted us to undertake a full description of the contributions of anisotropies involving high-order terms seldom seen when analyzing rocks or granular media. Instead of simplifying particles' shape and size variability, we modelled the complexity of these materials in order to identify the microstructural elements responsible for the macroscopic phenomena. We found that geometrical and mechanical anisotropies present complex compensations, which means they are not the main source of the failure strength variations. Rather, it is the cell coordination, the average branch length, and the average radial forces that present the larger fluctuations - making them the key microstructural elements at the origin of the macroscopic failure strength.

Real materials are tremendously complex. Through this work, we sought to explore this complexity with the most detailed parameters we could gather linked to the granular stress tensor. Note that the circular shape we used for the samples was simply a choice of configuration that allowed us to compare our results to those obtained in rock testing. Our approach, however, is general and can be extended to any sample shape, assemblies of many crushable bodies, and diverse bonding behavior other than pure cohesive. Another very interesting perspective deals with the mechanics of porous rocks or grains for which our numerical model can be modified to not only reproduce adjacent cell configurations, but structures with holes in it. Many questions remain unresolved concerning the compaction or shear properties (rheology) of assemblies composed of several crushable inherently anisotropic bodies, which would benefit from future research.

Acknowledgments

This research work benefited from the financial support of the Natural Sciences and Engineering Research Council of Canada (NSERC) [Ref. RGPIN-2019-06118], the Fonds de recherche du Québec - Nature et technologies (FRQNT) through the Programme de recherche en partenariat sur le développement durable du secteur minier-II [Ref. 2020-MN-281267] and the industrial partners of the Research Institute on Mines and the Environment (RIME) UQAT-Polytechnique (irme.ca/en). This research was enabled in part by support provided by Compute Canada (www.computeCanada.ca) under the Resources for Research Groups 2021 program (Project ID 3604). We also thank Franny McGill for her careful editing of the manuscript.

References

- [1] A. A. Griffith, The Phenomena of Rupture and Flow in Solids, *Philosophical Transactions of the Royal Society A: Mathematical, Physical and Engineering Sciences* 221 (1921) 163–198.
- [2] J. Jaeger, N. Cook, R. Zimmerman, *Fundamentals of Rock Mechanics*, Wiley, 2007.
- [3] E. Hoek, Fracture of Anisotropic Rock, *Journal of the South African Institute of Mining and Metallurgy* 64 (1964) 501–518.
- [4] M. Oda, Fabric tensor for discontinuous geological materials, *Soils and Foundations* 22 (1982).
- [5] B. Amadei, Importance of anisotropy when estimating and measuring in situ stresses in rock, *Int. J. Rock Mech. Min. Sci* 33 (1996) 293–325.
- [6] C.-S. Chen, E. Pan, B. Amadei, Determination of Deformability and Tensile Strength of Anisotropic Rock Using Brazilian Tests, *Int. J. Rock Mech. Min. Sci* 35 (1998) 43–61.
- [7] L. Zhang, H. H. Einstein, Estimating the intensity of rock discontinuities, *Int. J. Rock Mech. Min. Sci* 37 (2000) 819–837.
- [8] H. Karakul, R. Ulusay, N. S. Isik, Empirical models and numerical analysis for assessing strength anisotropy based on block punch index

- and uniaxial compression tests, *Int. J. Rock Mech. Min. Sci* 47 (2010) 657–665.
- [9] G. Khanlari, B. Rafei, Y. Abdilor, An Experimental Investigation of the Brazilian Tensile Strength and Failure Patterns of Laminated Sandstones, *Rock Mech. Rock Eng.* 48 (2015) 843–852.
 - [10] D. Guha Roy, T. N. Singh, Effect of Heat Treatment and Layer Orientation on the Tensile Strength of a Crystalline Rock Under Brazilian Test Condition, *Rock Mech. Rock Eng.* 49 (2016) 1663–1677.
 - [11] M. Pouragha, M. Eghbalian, R. Wan, Micromechanical correlation between elasticity and strength characteristics of anisotropic rocks, *Int. J. Rock Mech. Min. Sci* 125 (2020) 104154.
 - [12] H. Saroglou, G. Tsiambaos, A modified Hoek-Brown failure criterion for anisotropic intact rock, *Int. J. Rock Mech. Min. Sci* 45 (2008) 223–234.
 - [13] O. Saeidi, V. Rasouli, R. G. Vaneghi, R. Gholami, S. R. Torabi, A modified failure criterion for transversely isotropic rocks, *Geoscience Frontiers* 5 (2014) 215–225.
 - [14] M. Garagon, T. Çan, Predicting the strength anisotropy in uniaxial compression of some laminated sandstones using multivariate regression analysis, *Materials and Structures/Materiaux et Constructions* 43 (2010) 509–517.
 - [15] G. Xu, M. Gutierrez, C. He, W. Meng, Discrete element modeling of transversely isotropic rocks with non-continuous planar fabrics under Brazilian test, *Acta Geotechnica* 7 (2020).
 - [16] R. C. Hurley, J. Lind, D. C. Pagan, M. C. Akin, E. B. Herbold, In situ grain fracture mechanics during uniaxial compaction of granular solids, *J. Mech. Phys. Solids* 112 (2018) 273–290.
 - [17] F. Marinelli, G. Buscarnera, Anisotropic breakage mechanics: From stored energy to yielding in transversely isotropic granular rocks, *J. Mech. Phys. Solids* 129 (2019) 1–18.
 - [18] B. Indraratna, W. Salim, C. Rujikiatkamjorn, Advanced rail geotechnology-ballasted track, CRS Press, 2011.

- [19] W. L. Lim, G. R. McDowell, A. C. Collop, The application of Weibull statistics to the strength of railway ballast, *Granular Matter* 6 (2004) 229–237.
- [20] R. Marsal, Mechanical properties of rockfill dams, ISTE Ltd and John Wiley & Sons Inc., 1973.
- [21] C. Ovalle, E. Frossard, C. Dano, W. Hu, S. Maiolino, P. Y. Hicher, The effect of size on the strength of coarse rock aggregates and large rockfill samples through experimental data, *Acta Mechanica* 225 (2014) 2199–2216.
- [22] C. Ovalle, S. Linero, C. Dano, E. Bard, P.-Y. Hicher, R. Osses, Data Compilation from Large Drained Compression Triaxial Tests on Coarse Crushable Rockfill Materials, *J. of Geotech. Geoenviron. Eng.* 146 (2020) 06020013.
- [23] E. Favier, V. Lazarus, J.-B. Leblond, Statistics of the deformation of the front of a tunnel-crack propagating in some inhomogeneous medium, *J. Mech. Phys. Solids* 54 (2006) 1449 – 1478.
- [24] N. Pindra, V. Lazarus, J.-B. Leblond, Geometrical disorder of the fronts of a tunnel-crack propagating in shear in some heterogeneous medium, *J. Mech. Phys. Solids* 58 (2010) 281 – 299.
- [25] E. Bard, M. E. Anabalón, J. Campaña, Waste Rock Behavior at High Pressures: Dimensioning High Waste Rock Dumps, *Multiscale Geomechanics* (2013) 83–112.
- [26] R. Brzesowsky, S. Hangx, N. Brantut, C. Spiers, Compaction creep of sands due to time-dependent grain failure: Effects of chemical environment, applied stress, and grain size, *Journal of Geophysical Research, Solid Earth* 119 (2014) 7521–7541.
- [27] I. G. Main, P. G. Meredith, Stress corrosion constitutive laws as a possible mechanism of intermediate-term and short-term seismic quiescence, *Geophysical Journal International* 107 (1991) 363–372.
- [28] C. Sammis, G. King, R. Biegel, The kinematics of gouge deformation, *Pure and Applied Geophysics PAGEOPH* 125 (1987) 777–812.

- [29] L. Turcotte, Fractals and Fragmentation, *Journal of Geophysical Research* 91 (1986) 1921–1926.
- [30] I. Einav, Breakage mechanics-Part I: Theory, *J. Mech. Phys. Solids* 55 (2007) 1274–1297.
- [31] C. Ovalle, C. Voivret, C. Dano, P.-Y. Hicher, Population balance in confined comminution using a physically based probabilistic approach for polydisperse granular materials, *Int. J. Numer. Anal. Methods Geomech.* 40 (2016) 2383–2397.
- [32] Y. Zhang, G. Buscarnera, Breakage mechanics for granular materials in surface-reactive environments, *J. Mech. Phys. Solids* 112 (2018) 89–108.
- [33] E. Berthier, M. A. Porter, K. E. Daniels, Forecasting failure locations in 2-dimensional disordered lattices, *Proceedings of the National Academy of Sciences* 116 (2019) 16742–16749.
- [34] J. Sulem, M. Cerrolaza, Finite element analysis of the indentation test on rocks with microstructure, *Computers and Geotechnics* 29 (2002) 95–117.
- [35] S. Amir Reza Beyabanaki, A. Jafari, S. Omid Reza Biabanaki, M. Ronald Yeung, Nodal-based three-dimensional discontinuous deformation analysis (3-D DDA), *Computers and Geotechnics* 36 (2009) 359–372.
- [36] D. O. Potyondy, P. A. Cundall, A bonded-particle model for rock, *Int. J. Rock Mech. Min. Sci* 41 (2004) 1329–1364.
- [37] N. Cho, C. Martin, D. Sego, A clumped particle model for rock, *Int. J. Rock Mech. Min. Sci* 44 (2007) 997–1010.
- [38] H. Lan, C. D. Martin, B. Hu, Effect of heterogeneity of brittle rock on micromechanical extensile behavior during compression loading, *Journal of Geophysical Research* 115 (2010).
- [39] L. Scholtès, F. V. Donzé, A DEM model for soft and hard rocks: Role of grain interlocking on strength, *J. Mech. Phys. Solids* 61 (2013) 352–369.

- [40] T. Kazerani, Effect of micromechanical parameters of microstructure on compressive and tensile failure process of rock, *Int. J. Rock Mech. Min. Sci* 64 (2013) 44–55.
- [41] F. Q. Gao, D. Stead, The application of a modified Voronoi logic to brittle fracture modelling at the laboratory and field scale, *Int. J. Rock Mech. Min. Sci* 68 (2014) 1–14.
- [42] D. Cantor, N. Estrada, E. Azéma, Split-Cell Method for grain fragmentation, *Computers and Geotechnics* 67 (2015) 150–156.
- [43] M. Ciantia, M. Arroyo, F. Calvetti, A. Gens, An approach to enhance efficiency of DEM modelling of soils with crushable grains, *Geotechnique* (2015) 91–110.
- [44] A. Gladkyy, M. Kuna, DEM simulation of polyhedral particle cracking using a combined Mohr–Coulomb–Weibull failure criterion, *Granular Matter* 19 (2017) 1–11.
- [45] P. S. Iliev, F. K. Wittel, H. J. Herrmann, Evolution of fragment size distributions from the crushing of granular materials, *Phys. Rev. E* 99 (2019) 1–10.
- [46] O. K. Mahabadi, B. E. Cottrell, G. Grasselli, An example of realistic modelling of rock dynamics problems: FEM/DEM simulation of dynamic brazilian test on Barre Granite, *Rock Mech. Rock Eng.* 43 (2010) 707–716.
- [47] A. Bagherzadeh Kh., A. Mirghasemi, S. Mohammadi, Numerical simulation of particle breakage of angular particles using combined DEM and FEM, *Powder Technology* 205 (2011) 15–29.
- [48] N. Guo, J. Zhao, A coupled FEM/DEM approach for hierarchical multiscale modelling of granular media, *International journal for numerical methods in engineering* 99 (2014) 789–818.
- [49] G. Ma, W. Zhou, X. L. Chang, W. Yuan, Combined FEM/DEM modeling of triaxial compression tests for rockfills with polyhedral particles, *International Journal of Geomechanics* 14 (2014) 1–12.

- [50] X. Tan, H. Konietzky, T. Frühwirth, D. Q. Dan, Brazilian Tests on Transversely Isotropic Rocks: Laboratory Testing and Numerical Simulations, *Rock Mech. Rock Eng.* 48 (2015) 1341–1351.
- [51] O. Tsoungui, D. Vallet, J. C. Charmet, Numerical model of crushing of grains inside two-dimensional granular materials, *Powder Technology* 105 (1999) 190–198.
- [52] S. Lobo-Guerrero, L. E. Vallejo, Influence of pile shape and pile interaction on the crushable behavior of granular materials around driven piles: DEM analyses, *Granular Matter* 9 (2007) 241–250.
- [53] Y. Jiang, P. Mora, H. J. Herrmann, F. Alonso-Marroquín, Damage separation model: A replaceable particle method based on strain energy field, *Phys. Rev. E* 104 (2021) 045311.
- [54] F. Zhu, J. Zhao, Interplays between particle shape and particle breakage in confined continuous crushing of granular media, *Powder Technology* 378 (2021) 455–467.
- [55] Y. Cheng, M. Bolton, Y. Nakata, Crushing and plastic deformation of soils simulated using DEM, *Geotechnique* (2004) 131–141.
- [56] J. Lin, E. Bauer, W. Wu, A combined method to model grain crushing with dem, *Geoscience Frontiers* 11 (2020) 451–459. Grain Crushing in Geoscience Materials.
- [57] L. M. Tavares, V. A. Rodriguez, M. Sousani, C. B. Padros, J. Y. Ooi, An effective sphere-based model for breakage simulation in dem, *Powder Technology* 392 (2021) 473–488.
- [58] J. P. De Bono, G. R. McDowell, Discrete element modelling of one-dimensional compression of cemented sand, *Granular Matter* 16 (2014) 79–90.
- [59] W. Zhou, D. Wang, G. Ma, X. Cao, C. Hu, W. Wu, Discrete element modeling of particle breakage considering different fragment replacement modes, *Powder Technology* 360 (2020) 312–323.
- [60] D.-H. Nguyen, E. Azéma, P. Sornay, F. Radjai, Bonded-cell model for particle fracture, *Phys. Rev. E* 91 (2015) 022203.

- [61] D. Cantor, E. Azéma, P. Sornay, F. Radjai, Three-dimensional bonded-cell model for grain fragmentation, *Computational Particle Mechanics* 4 (2017) 441–450.
- [62] L. F. Orozco, J. Y. Delenne, P. Sornay, F. Radjai, Discrete-element model for dynamic fracture of a single particle, *Int. J. Solids Struct.* 166 (2019) 47–56.
- [63] Y. Huilca, M. Silva, C. Ovalle, S. Carrasco, J. Quezada, G. Villavicencio, Modeling size effect on rock aggregates strength using a DEM bonded-cell model, *Acta Geotechnica* (2020).
- [64] Q. Du, M. Emelianenko, L. Ju, Convergence properties of the lloyd algorithm for computing the centroidal voronoi tessellations, *SIAM Journal on Numerical Analysis* 44 (2006) 102–119.
- [65] D. R. Jones, M. F. Ashby, *Engineering materials 1*, Butterworth-Heinemann, 2019.
- [66] Cantor, David, Ovalle, Carlos, Azéma, Emilien, Strength and energy consumption of inherently anisotropic rocks at failure, *EPJ Web Conf.* 249 (2021) 07003.
- [67] M. Jean, The non-smooth contact dynamics method, *Computer Methods in Applied Mechanics and Engineering* 177 (1999) 235–257.
- [68] F. Dubois, V. Acary, M. Jean, The Contact Dynamics method: A nonsmooth story, *Comptes Rendus - Mécanique* 346 (2018) 247–262.
- [69] M. Renouf, F. Dubois, P. Alart, A parallel version of the non smooth contact dynamics algorithm applied to the simulation of granular media, *J. Comput. Appl. Math.* 168 (2004) 375–382.
- [70] F. Radjai, V. Richefeu, Contact dynamics as a nonsmooth discrete element method, *Mechanics of Materials* 41 (2009) 715–728.
- [71] G. Saussine, C. Cholet, P. Gautier, F. Dubois, C. Bohatier, J. Moreau, Modelling ballast behaviour under dynamic loading. Part 1: A 2D polygonal discrete element method approach, *Computer Methods in Applied Mechanics and Engineering* 195 (2006) 2841–2859.

- [72] F. Dubois, M. Jean, M. Renouf, R. Mozul, A. Martin, M. Bagn  ris, LMGC90, in: 10e colloque national en calcul des structures, 2011, p. 8 p.
- [73] F. Dubois, M. Jean, et al, LMGC90 wiki page, https://git-xen.lmgc.univ-montp2.fr/lmgc90/lmgc90_user/wikis/home, 2020. [Online; accessed 17-Jul-2020].
- [74] Y. Hiramatsu, Y. Oka, Determination of the tensile strength of rock by a compression test of an irregular test piece, *Int. J. Rock Mech. Min. Sci* 3 (1966) 89 – 90.
- [75] J. Jaeger, Failure of rocks under tensile conditions, *Int. J. Rock Mech. Min. Sci* 4 (1967) 219 – 227.
- [76] G. R. McDowell, M. D. Bolton, On the micromechanics of crushable aggregates, *Geotechnique* 48 (1998) 667–679.
- [77] G. McDowell, A. Amon, The application of weibull statistics to the fracture of soil particles, *Soils and Foundations* 40 (2000) 133–141.
- [78] Y. Nakata, Y. Kato, M. Hyodo, A. F. Hyde, H. Murata, One-dimensional compression behaviour of uniformly graded sand related to single particle crushing strength, *Soils and Foundations* 41 (2001) 39–51.
- [79] G. McDowell, On the yielding and plastic compression of sand, *Soils and Foundations* 42 (2002) 139–145.
- [80] E. Az  ma, F. Radjai, Stress-strain behavior and geometrical properties of packings of elongated particles, *Phys. Rev. E* 81 (2010).
- [81] L. Rothenburg, R. J. Bathurst, Analytical study of induced anisotropy in idealized granular material, *G  otechnique* 39 (1989) 601–614.
- [82] B. Andreotti, Y. Forterre, O. Pouliquen, *Granular media: between fluid and solid*, Cambridge University press, 2013.
- [83] F. Nicot, N. Hadda, M. Guessedas, J. Fortin, O. Millet, On the definition of the stress tensor in granular media, *Int. J. Solids Struct.* 50 (2013) 2508 – 2517.

- [84] H. C. H. Rumpf, Zur theorie der zugfestigkeit von agglomeraten bei kraftübertragung an kontaktpunkten, Chemie Ingenieur Technik 42 (1970) 538–540.
- [85] T. Gröger, U. Tüzün, D. M. Heyes, Modelling and measuring of cohesion in wet granular materials, Powder Technology 133 (2003) 203 – 215.
- [86] V. Richefeu, M. S. El Youssoufi, F. Radjai, Shear strength properties of wet granular materials, Phys. Rev. E 73 (2006) 051304.