

**Amorphous multimetal based catalyst for oxygen evolution reaction**

*Zishuai Zhang<sup>#</sup>, Daniela Vieira<sup>#</sup>, Jake E Barralet<sup>‡</sup>, Geraldine Merle<sup>‡\*</sup>*

Z. Zhang, D. Vieira, Prof. J. E. Barralet, Prof. G. Merle

Faculty of Medicine, McGill University, Montreal, H3A 0C5, Canada

Current affiliation Prof. G. Merle,

Email: [geraldine.merle@polymtl.ca](mailto:geraldine.merle@polymtl.ca)

Chemical Engineering Department, Ecole Polytechnique de Montréal, P.O. Box 6079 Station,  
Montreal, QC H3C 3A7, Canada

<sup>#</sup> These authors contributed equally to this work

\* Corresponding author

**Table S1.** Compositions for screening NiCoV catalysts and their corresponding potentials at the current density of 10 mA cm<sup>-2</sup>.

Samples	Ni <sup>2+</sup> (at. %)	Co <sup>2+</sup> (at. %)	VO <sup>2+</sup> (at. %)	$\eta$ (10 mA cm <sup>-2</sup> ) (V vs. RHE)	Tafel slope (mV dec <sup>-1</sup> )
1	100	0	0	1.53	215
2	0	100	0	1.57	151
3	40	60	0	1.59	290
4	15	80	5	1.52	168
5	10	85	5	1.51	168
6	80	10	10	1.57	214
7	60	30	10	1.57	202
8	30	60	10	1.51	161
9	10	80	10	1.48	130
10	5	85	10	1.49	156
11	5	80	15	1.51	142
12	10	75	15	1.52	157
13	25	40	35	1.52	177
14	35	30	35	1.54	163
15	30	35	35	1.54	172

16	25	40	35	1.53	157
17	20	45	35	1.56	168
18	10	50	40	1.57	152
19	20	40	40	1.56	164
20	30	30	40	1.58	193
21	40	20	40	1.73	260
22	50	10	40	1.74	270
23	25	35	40	1.61	166
24	15	45	40	1.59	167
25	60	0	40	1.76	420
26	0	60	40	1.57	157
27	50	0	50	1.8	450
28	40	10	50	1.74	222
29	10	40	50	1.59	172
30	20	30	50	1.58	173
31	30	20	50	1.69	216
32	20	10	70	1.69	206
33	10	20	70	1.65	187

34	0	0	100	>1,70	>500
----	---	---	-----	-------	------

**Table S2.** Compositions of single metallic catalysts (Ni, Co, V), binary metallic catalysts (NiCo, NiV, CoV) and ternary metallic catalysts (NiCoV).


Catalyst abbreviation	Ni <sup>2+</sup> (at. %)	Co <sup>2+</sup> (at. %)	VO <sup>2+</sup> (at. %)
<b>Ni</b>	100	0	0
<b>Co</b>	0	100	0
<b>V</b>	0	0	100
<b>NiCo</b>	40	60	0
<b>NiV</b>	60	0	40
<b>CoV</b>	0	60	40
<b>NiCoV</b>	10	80	10

**Table S3.** Summary of the OER overpotentials (at a current density of 10mA cm<sup>-2</sup>) and Tafel slope of reported Co- and Ni- based OER catalysts.


Catalyst	Substrate	Solution	Overpotential (mA, at 10mA cm <sup>-2</sup> )	Tafel slope	Ref.
NiCoV/mesh	Stainless steel mesh	1M KOH	220	40	This work
RuO <sub>2</sub> /mesh	Stainless steel mesh	1M KOH	190	73	This work

Ni <sub>3</sub> S <sub>2</sub> /NF	Ni foam	1M KOH	350	108	[1]
CoS <sub>2</sub> nanoparticles	Ni foam	1M KOH	430	81.4	[2]
CoSe <sub>2</sub> nanoparticles	Ni foam	1M KOH	424	78.3	[2]
Co(S <sub>0.22</sub> Se <sub>0.78</sub> ) <sub>2</sub>	Ni foam	1M KOH	283	65.6	[2]
MoS <sub>2</sub> / Ni <sub>3</sub> S <sub>2</sub>	Ni foam	1M KOH	218	88	[3]
Ni <sub>2</sub> P nanoparticles	Glassy carbon	1M KOH	290	59	[4]
FeNiO	Ni foam	1M KOH	297	37	[5]
NiCoP/C nanobox	Glassy carbon	1M KOH	330	115	[6]
Ni <sub>3</sub> FeN nanosheets	Glassy carbon	1M KOH	280	46	[7]
Ni <sub>3</sub> B	Glassy carbon	1M KOH	302	52	[8]

NiCo <sub>2</sub> O <sub>4</sub> nanowires	Conductive electrode	1M KOH	460	90	[9]
Co <sub>9-x</sub> Ni <sub>x</sub> S <sub>8</sub> nanocages	Conductive electrode	1M NaOH	364	74.7	[10]
P-Co <sub>3</sub> O <sub>4</sub>	Conductive electrode	1M KOH	280	51.6	[11]


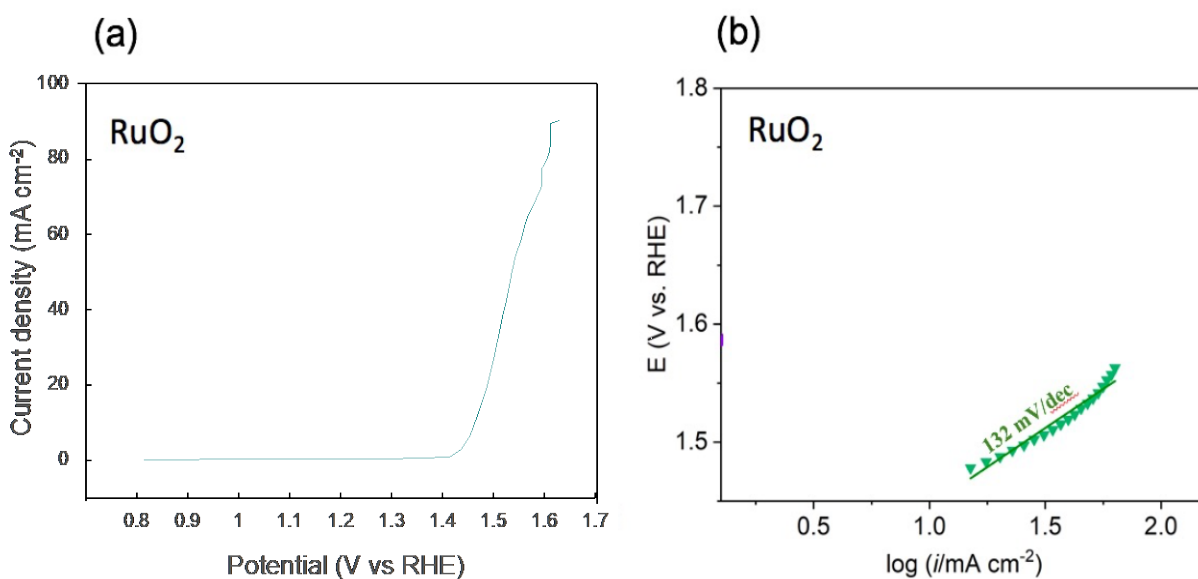


**Figure S1.** Electrochemical performance of RuO<sub>2</sub> catalysts on glassy carbon electrodes. (a) polarization curves of oxygen evolution reaction for different catalysts at a scan rate of 20 mV s<sup>-1</sup> in 1M KOH, and (b) Tafel slopes of RuO<sub>2</sub> catalysts on glassy carbon electrodes.


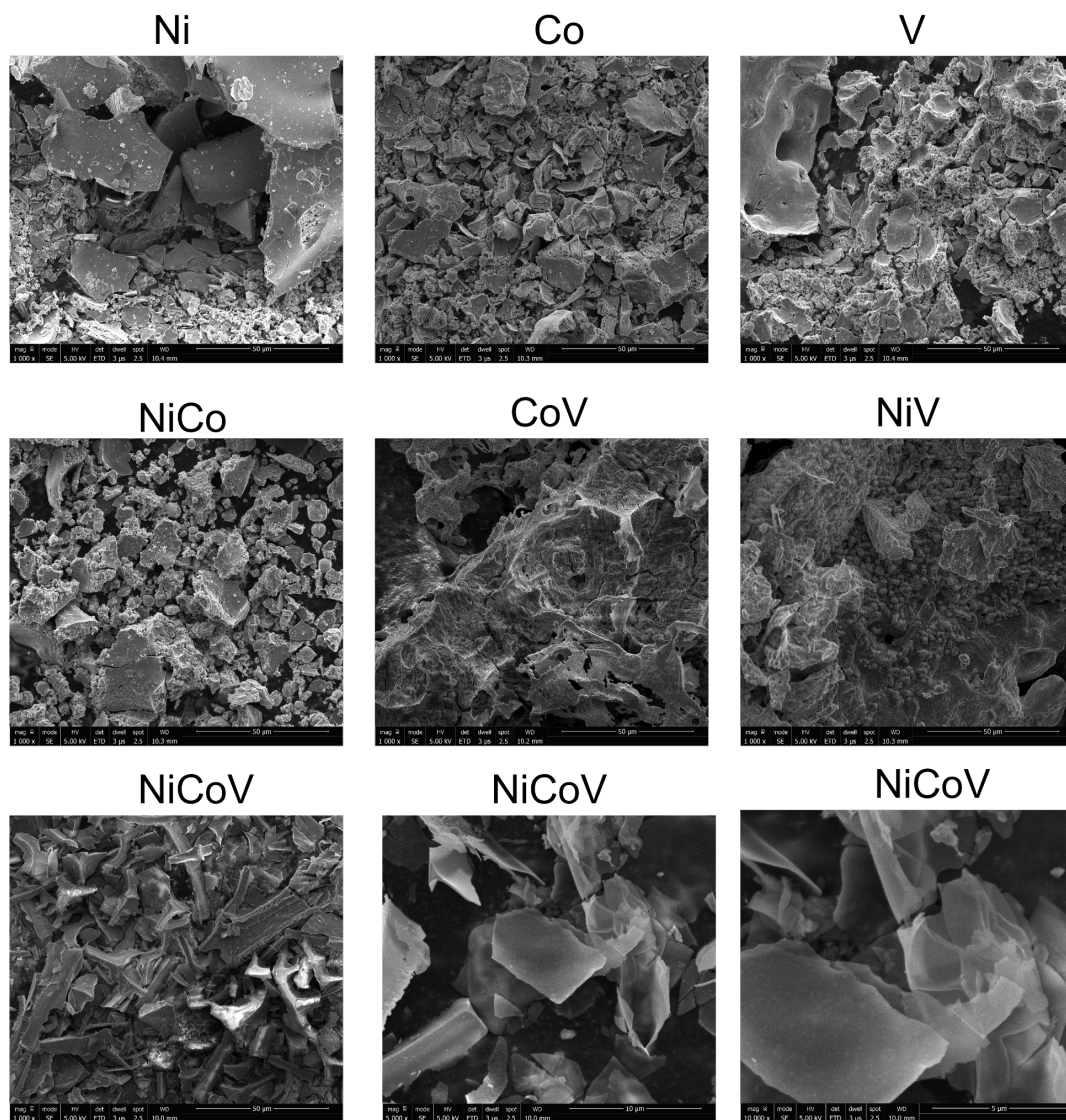


**Figure S2.** SEM images of various components of Ni, Co, V based catalysts. See details about each sample component in Table S2.

NiCo

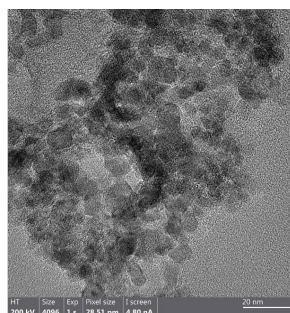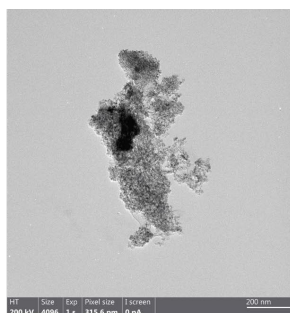

NiV

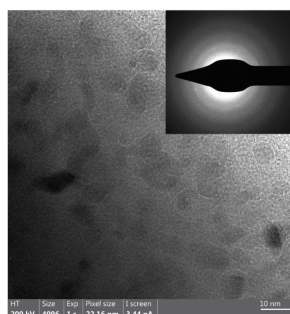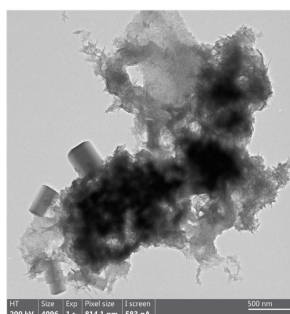

CoV




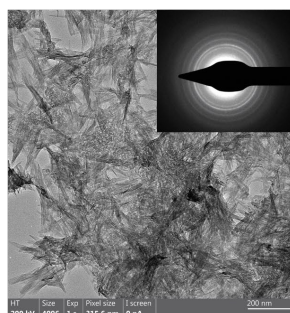


Figure S3. TEM images of NiCo, NiV and CoV.

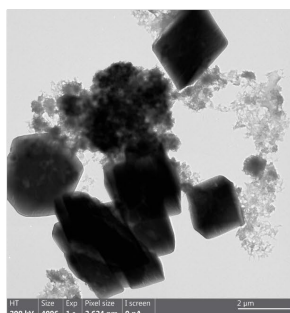


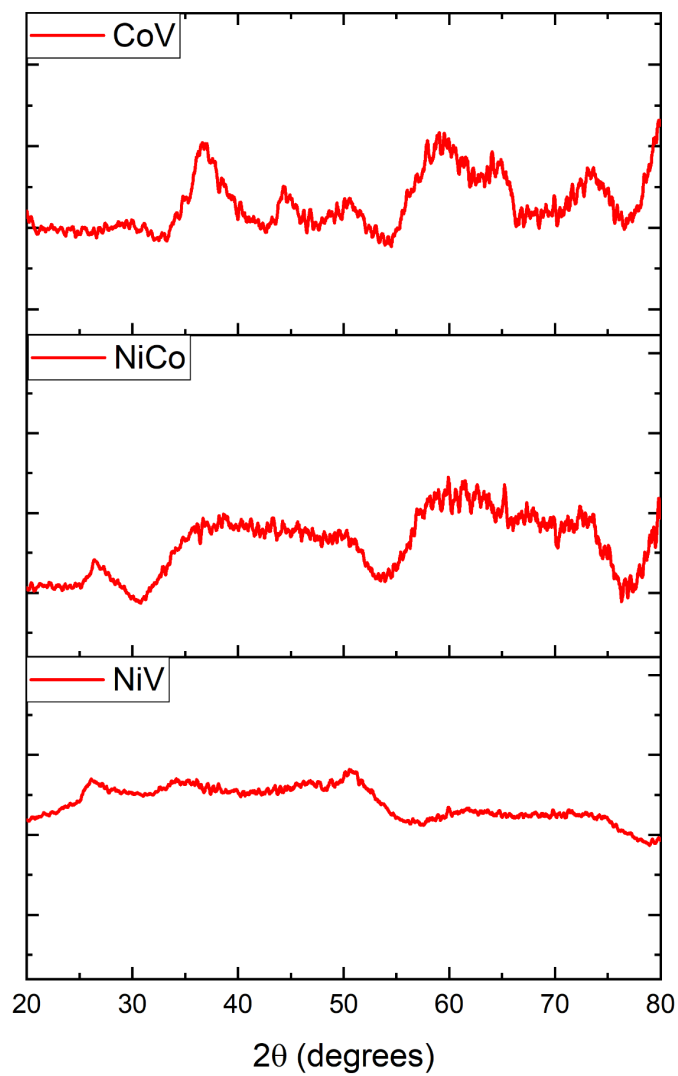


**Figure S4.** XRD patterns of **CoV**, **NiCo** and **NiV** samples. **NiV** shows less pronounced crystalline structure compared to **NiCo** and **CoV**.

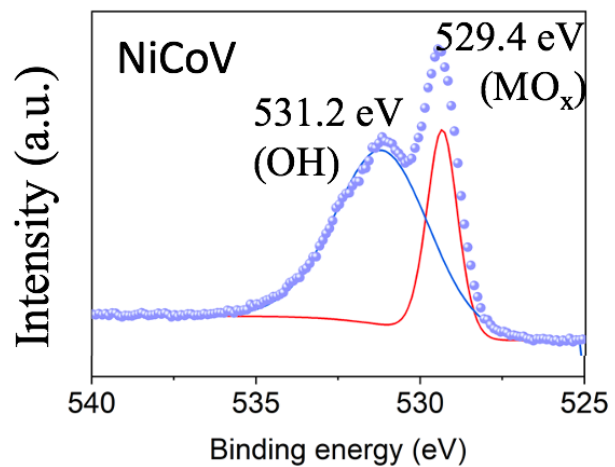


**Figure S5.** High resolution XPS spectra of O 1s for the NiCoV sample.

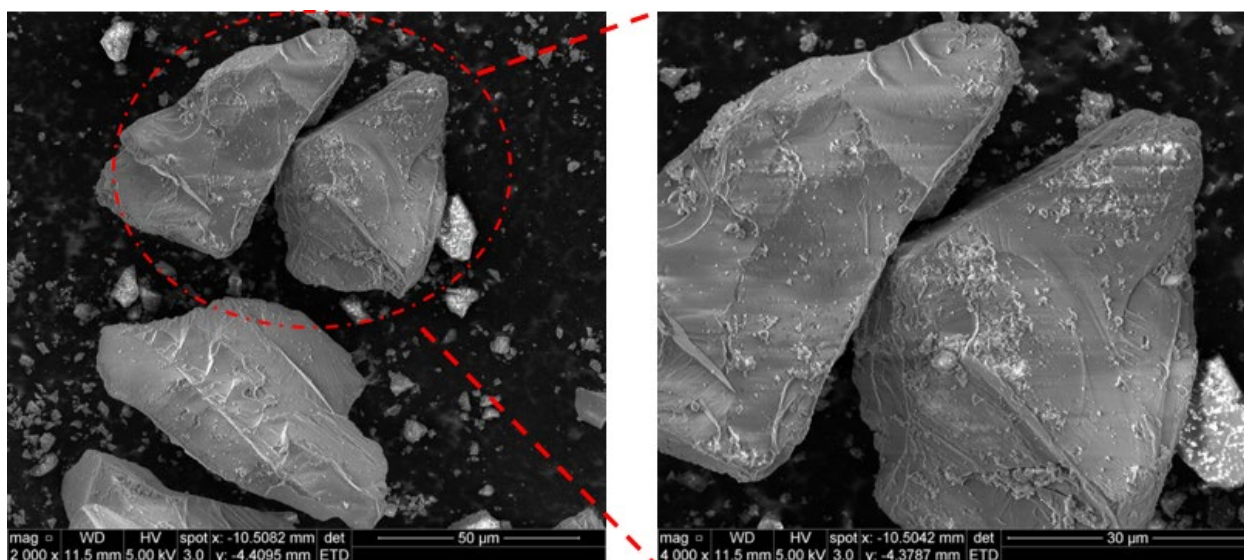

**Figure S6.** SEM images of corundum coated by NiCoV catalyst.

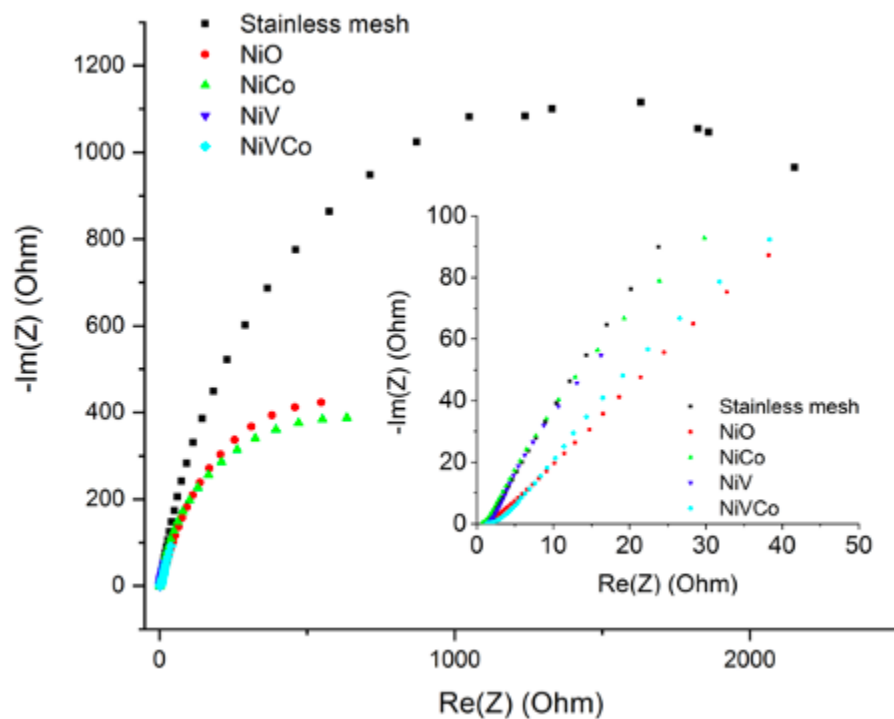

**Figure S7.** Nyquist plots of blank mesh, Ni, NiCo, NiV and NiCoV coated meshes.

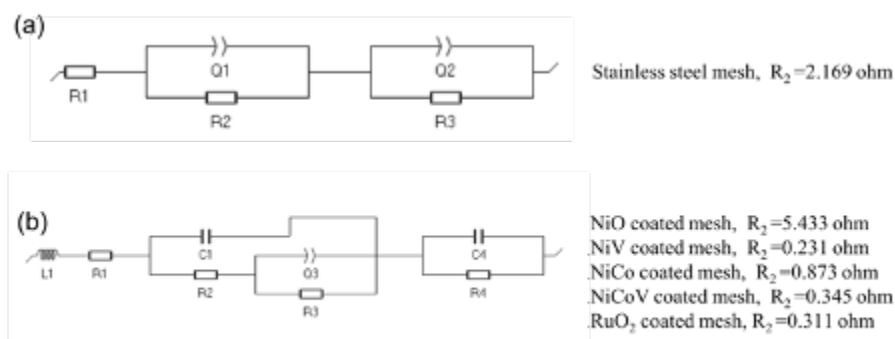

**Figure S8.** Corresponding equivalent electrical circuits for stainless steel mesh (a) and catalyst coated mesh (b) based on the Nyquist plots.

- [1] M. Dincă, Y. Surendranath, D.G. Nocera, Nickel-borate oxygen-evolving catalyst that functions under benign conditions, Proc. Natl. Acad. Sci. U. S. A. 107 (2010) 10337–10341.
- [2] L. Fang, W. Li, Y. Guan, Y. Feng, H. Zhang, S. Wang, Y. Wang, Tuning unique peapod-like co(S x Se1- x )<sub>2</sub> nanoparticles for efficient overall water splitting, Adv. Funct. Mater. 27 (2017) 1701008.
- [3] J. Zhang, T. Wang, D. Pohl, B. Rellinghaus, R. Dong, S. Liu, X. Zhuang, X. Feng, Interface Engineering of MoS<sub>2</sub> /Ni<sub>3</sub> S<sub>2</sub> Heterostructures for Highly Enhanced Electrochemical

- Overall-Water-Splitting Activity, *Angewandte Chemie International Edition*. 55 (2016) 6702–6707. <https://doi.org/10.1002/anie.201602237>.
- [4] L.-A. Stern, L. Feng, F. Song, X. Hu, Ni<sub>2</sub>P as a Janus catalyst for water splitting: the oxygen evolution activity of Ni<sub>2</sub>P nanoparticles, *Energy & Environmental Science*. 8 (2015) 2347–2351. <https://doi.org/10.1039/c5ee01155h>.
- [5] K. Fominykh, P. Chernev, I. Zaharieva, J. Sicklinger, G. Stefanic, M. Döblinger, A. Müller, A. Pokharel, S. Böcklein, C. Scheu, T. Bein, D. Fattakhova-Rohlfing, Iron-doped nickel oxide nanocrystals as highly efficient electrocatalysts for alkaline water splitting, *ACS Nano*. 9 (2015) 5180–5188.
- [6] B. Liu, H.-Q. Peng, C.-N. Ho, H. Xue, S. Wu, T.-W. Ng, C.-S. Lee, W. Zhang, Mesoporous Nanosheet Networked Hybrids of Cobalt Oxide and Cobalt Phosphate for Efficient Electrochemical and Photoelectrochemical Oxygen Evolution, *Small*. 13 (2017). <https://doi.org/10.1002/smll.201701875>.
- [7] X. Jia, Y. Zhao, G. Chen, L. Shang, R. Shi, X. Kang, G.I.N. Waterhouse, L.-Z. Wu, C.-H. Tung, T. Zhang, Ni<sub>3</sub>FeN Nanoparticles Derived from Ultrathin NiFe-Layered Double Hydroxide Nanosheets: An Efficient Overall Water Splitting Electrocatalyst, *Adv. Energy Mater.* 6 (2016) 1502585.
- [8] W.-J. Jiang, S. Niu, T. Tang, Q.-H. Zhang, X.-Z. Liu, Y. Zhang, Y.-Y. Chen, J.-H. Li, L. Gu, L.-J. Wan, J.-S. Hu, Crystallinity-modulated electrocatalytic activity of a nickel(II) borate thin layer on Ni<sub>3</sub>B for efficient water oxidation, *Angew. Chem. Int. Ed Engl.* 56 (2017) 6572–6577.
- [9] X. Yu, Z. Sun, Z. Yan, B. Xiang, X. Liu, P. Du, Direct growth of porous crystalline NiCo<sub>2</sub>O<sub>4</sub> nanowire arrays on a conductive electrode for high-performance electrocatalytic water oxidation, *J. Mater. Chem. A*. 2 (2014) 20823–20831. <https://doi.org/10.1039/c4ta05315j>.
- [10] J. Kim, H. Jin, A. Oh, H. Baik, S.H. Joo, K. Lee, Synthesis of compositionally tunable, hollow mixed metal sulphide Co<sub>x</sub>Ni<sub>y</sub>S<sub>z</sub> octahedral nanocages and their composition-dependent electrocatalytic activities for oxygen evolution reaction, *Nanoscale*. 9 (2017) 15397–15406.
- [11] Z. Xiao, Y. Wang, Y.-C. Huang, Z. Wei, C.-L. Dong, J. Ma, S. Shen, Y. Li, S. Wang, Filling the oxygen vacancies in Co<sub>3</sub>O<sub>4</sub> with phosphorus: an ultra-efficient electrocatalyst for overall water splitting, *Energy Environ. Sci.* 10 (2017) 2563–2569.