

Titre: On the mechanical behavior of vacuum applied surface treatments
Title:

Auteurs: Annie Ross, Jean-Frédéric Roy, & Germain Ostiguy
Authors:

Date: 2002

Type: Article de revue / Article

Référence: Ross, A., Roy, J.-F., & Ostiguy, G. (2002). On the mechanical behavior of vacuum applied surface treatments. Canadian acoustics, 30(2), 62-63. Présentée à Semaine canadienne d'acoustique 2002, Charlottetown, Île-du-Prince-Édouard, Canada. <https://jcaa.caa-aca.ca/index.php/jcaa/article/view/1455>
Citation:

Document en libre accès dans PolyPublie

Open Access document in PolyPublie

URL de PolyPublie: <https://publications.polymtl.ca/82971/>
PolyPublie URL:

Version: Version officielle de l'éditeur / Published version
Révisé par les pairs / Refereed

Conditions d'utilisation: Author Licensing Addendum
Terms of Use:

Document publié chez l'éditeur officiel

Document issued by the official publisher

Titre de la revue: Canadian acoustics (vol. 30, no. 2)
Journal Title:

Maison d'édition: Canadian Acoustical Association
Publisher:

URL officiel: <https://jcaa.caa-aca.ca/index.php/jcaa/article/view/1455>
Official URL:

Mention légale: Author Licensing Addendum This Licensing Addendum ("Addendum") is entered into between the undersigned Author(s) and Canadian Acoustics journal published by the Canadian Acoustical Association (hereinafter referred to as the "Publisher"). The Author(s) and the Publisher agree as follows: Retained Rights: The Author(s) retain(s) the following rights: The right to reproduce, distribute, and publicly display the Work on the Author's personal website or the website of the Author's institution. The right to use the Work in the Author's teaching activities and presentations. The right to include the Work in a compilation for the Author's personal use, not for sale. Grant of License: The Author(s) grant(s) to the Publisher a worldwide exclusive license to publish, reproduce, distribute, and display the Work in Canadian Acoustics and any other formats and media deemed appropriate by the Publisher. Attribution: The Publisher agrees to include proper attribution to the Author(s) in all publications and reproductions of the Work. No Conflict: This Addendum is intended to be in harmony with, and not in conflict with, the terms and conditions of the original agreement entered into between the Author(s) and the Publisher. Copyright Clause: Copyright on articles is held by the Author(s). The
Legal notice:



corresponding Author has the right to grant on behalf of all Authors and does grant on behalf of all Authors, a worldwide exclusive license to the Publisher and its licensees in perpetuity, in all forms, formats, and media (whether known now or created in the future), including but not limited to the rights to publish, reproduce, distribute, display, store, translate, create adaptations, reprints, include within collections, and create summaries, extracts, and/or abstracts of the Contribution.

ON THE MECHANICAL BEHAVIOR OF VACUUM APPLIED SURFACE TREATMENTS

Annie Ross¹, Jean-Frédéric Roy¹, Germain Ostiguy²

¹Faculté d'ingénierie, Université de Moncton, Moncton, N.B. E1A 3E9 rossa@umoncton.ca

²Dept. Mech. Eng., École Polytechnique de Montréal, P.O.Box 6079, succ. Centre-ville, Montréal, Québec, H3C 3A7

1. INTRODUCTION

Surface treatments are sometimes used to reduce the amplitudes of vibration in large, shell-type structures (Nashif et al., 1985). The pads normally consist of a viscoelastic layer that may or may not be laminated with a thin constraining plate. When the pads are bonded onto the structure, additional damping is provided either through extensional (unconstrained) or shear dissipation (constrained pads) within the viscoelastic layer.

Viscoelastic damping pads are also used as a noise control element, owing to their ability for reducing transverse vibrations. However, in some applications such as aircraft skin assembly, adhesive bonded pads obviously may not be used. In these cases, a vacuum applied damping treatment can be used. It is bonded temporarily, and is removed once the skins are fastened, leaving no vestige on the aircraft.

Vacuum applied damping pads (VA pads) were shown to be quite efficient in reducing impact noises. However, when compared with traditional adhesive bonded pads, a major difference in the acoustic pressure time signal was observed, but was only partly explained (Ross, Amram, Ostiguy, 2001). In this paper, vibration measurements provide additional insight on the matter.

2. EXPERIMENTAL SETUP

Experiments were performed on a simply supported, rectangular aluminum plate. A steel, ball-ended hammer was used to strike the 0,9m x 0,6m x 4,8mm plate at its center point. VA pads were placed symmetrically at 25mm on either sides of the impact point.

One particular configuration was used as an extreme experimental case. In this configuration, the VA pads consisted of the single constraining layer. It was meant to show the effects of added mass and rigidity on the plate, without any viscoelastic damping. The two 1,5mm thick aluminum pads added an extra 31% to the thickness of the plate. A small degree of damping was possible through dry friction on the interface, as the pads were vacuum applied onto the plate.

3. NOISE MEASUREMENTS

During the impacts, the acoustic pressure was sampled at various points on a plane grid positioned 50mm from the surface of the plate. Figure 1 shows the data obtained at a measurement point located close to the impact axis (normal to the plate, passing through the impact point).

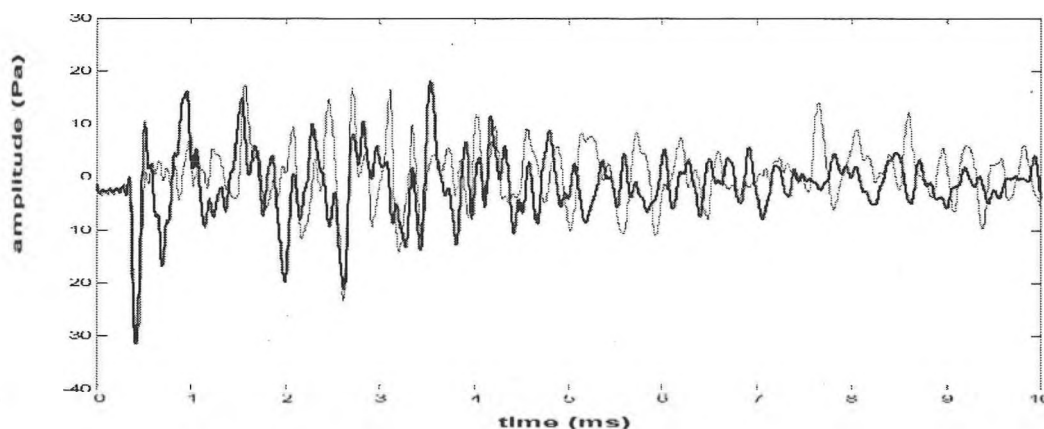


Fig. 1. Acoustic pressure along the impact axis (light: bare plate; dark: with VA pads).

The thin curve is the acoustic pressure due to the impacts on the bare plate (no pads). The acceleration peak is easily identified, and is followed by a "quiet" period before the ringing noise is established.

The thick curve is the acoustic pressure obtained when the VA pads were applied. These VA pads did not have a viscoelastic layer. The acceleration peak is similar to that of the bare plate. However, a large amplitude oscillation immediately follows this first peak and amplifies the radiated noise. This oscillation was previously thought to be the result of a local vibration of the plate between the two VA pads (Ross, Ostiguy, Amram, 2001).

4. VIBRATION MEASUREMENTS

Recent experimental work led to a better understanding of the phenomenon. Lightweight accelerometers were positioned at various locations on the system. Transverse vibrations of the plate were compared, with and without the VA pads. Figure 2 shows the transverse acceleration of the plate, measured at 50mm from the impact point. When the VA pads were used, the acceleration was measured both on the plate (back side) and on the pad (front side), at the same location as above.

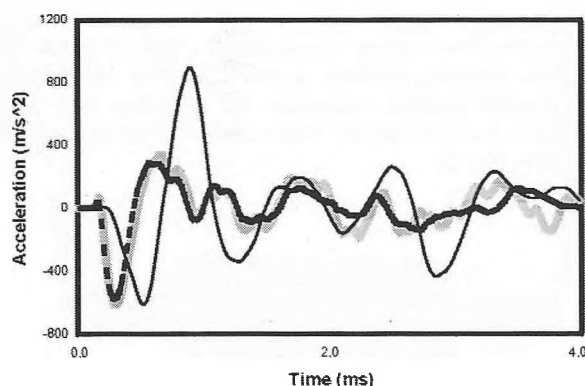


Fig. 2. Transverse acceleration of the plate at 50mm from the impact point (gray: bare plate; ---: plate with VA pads; —: VA pad).

It can be seen that for nearly 2ms, there are insignificant changes in the behavior of the plate, when the VA pads are applied. Changes that do occur seem to affect relatively high frequencies only.

The VA pad itself, however, does not seem to follow the movement of the plate. Its transverse acceleration signal shows that a very large oscillation exists at many but not all locations on the surface of the pad. It seems that the vacuum interface allows a certain amount of freedom to the VA pads, and some regions may temporarily separate from the plate (or may not be in contact at all). This may also hold

true for the viscoelastic VA pads, with a lesser degree since these ones are much heavier and more rigid than the constraining layer alone.

The vibration of the VA pads — and not that of the plate — seems to be the cause of the amplified acoustic pressure in the near field of the impacted plate. The VA pads therefore act as a second noise source, in addition to the plate.

5. CONCLUSIONS

It was shown, through experimental analysis, that the transverse acceleration of vacuum applied pads is partly independent of the motion of the impacted plate. In the future, a finite element analysis of the system should yield a complete view and better understanding of the motion of the pads. The use of Nearfield Acoustical Holography on such data would confirm the effect of this vibration on the sound pressure field. Observations and analysis should be performed on viscoelastic VA pads, in order to detect any similar behavior.

REFERENCES

- Nashif, A.D., Jones, D.I.G., Henderson, J.P. (1985). *Vibration Damping*. John Wiley & Sons, N.Y.
- Ross A., Amram M., Ostiguy G. (2001). Benefits of Vac Damps over adhesive bonded damping pads for impact noise control, *Applied Acoustics*, 62(7), pp.813-830.
- Ross A., Ostiguy G., Amram A. (2001). Effets d'une discontinuité d'épaisseur sur la propagation des ondes de flexion, *Proceedings 18th Canadian Congress of Applied Mechanics*, M.U.N., Vol.1, pp.51-52.

ACKNOWLEDGEMENTS

This work was supported in parts by the NSERC, the Department of Intergovernmental Affairs of the Province of N.B., and the Université de Moncton.

AUTHORS NOTE

The experimental work was conducted by A.R. and by J.-F.R. at the École Polytechnique de Montréal.